

Marginal Degradation of Universal Adhesive Restorations in NCCLs: A Systematic Review and Meta-analysis



Thaís Andrade de Figueiredo Barros¹, Elma Vieira Takeuchi^{1,*}, Cíntia de Melo Silva Souza¹, Aryvelto Miranda Silva², Cristiane de Melo Alencar³ and Cecy Martins Silva^{1,*}

¹Department of Restorative Dentistry, Dental School, Federal University of Pará, Rua Augusto Correa no. 1, cidade universitária José da Silveira Neto. Guamá, Belém, PA - CEP: 66075110, Pará, Brazil

²Department of Dentistry, Federal University of Juiz de Fora, Campus GV (UFJF-GV), Governador Valadares, Av. Moacir Paleta, 1167 - São Pedro, Governador Valadares, MG - CEP: 35020-360, Brazil

³Department of Restorative Dentistry, Centro Universitário do Estado do Pará (CESUPA), Trav. Nove de Janeiro, 927 - Fátima, Belém, PA - CEP: 66060-575, Pará, Brazil

Abstract:

Purpose: This systematic review aimed to answer the PICO question: do adhesive protocols used for non-carious cervical lesions (NCCLs) using a universal adhesive system influence marginal degradation, marginal staining, and retention of these restorations? The self-etching adhesive strategy and selective enamel etching were compared with the etch-and-rinse strategy as a control.

Materials and Methods: The study searched various databases, including PubMed, Web of Science, Cochrane Central Register of Controlled Trials, Scopus, Embase, and grey literature, to find randomized clinical trials (RCTs) comparing self-etching (SE) or selective enamel etching (SEE) to the etch and rinse (ER) strategy. The risk of methodological bias was assessed using the Cochrane RoB 2 tool. Data were dichotomized and analyzed using RevMan v 5.3, adopting the Mantel-Haenszel method. The quality of evidence was assessed using Grading of Recommendations Assessment, Development and Evaluation (GRADE).

Results: Twenty RCTs were included in the meta-analysis. Results showed that using universal adhesives with the SE strategy resulted in clinical signs of marginal degradation at 12 months, 24 months, and 36 months of follow-up, and marginal staining at 24 months. The adhesive strategy did not interfere with the retention of restorative material used for NCCLs over 36 months, as assessed based on both the United States Public Health Service (USPHS) and World Dental Federation (FDI) criteria.

Conclusion: With moderate certainty of evidence, after 24 months of follow-up, the SE strategy results in the detection of clinical signs of marginal degradation and staining. The adhesive strategy adopted did not influence the retention rate of the restorations over 36 months of follow-up.

Keywords: Non-carious cervical lesions, Universal adhesives, Dental bonding, Systematic review, Marginal adaptation, Marginal discoloration.

© 2024 The Author(s). Published by Bentham Open.

This is an open access article distributed under the terms of the Creative Commons Attribution 4.0 International Public License (CC-BY 4.0), a copy of which is available at: <https://creativecommons.org/licenses/by/4.0/legalcode>. This license permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

*Address correspondence to these authors at the Department of Restorative Dentistry, Dental School, Federal University of Pará, Rua Augusto Correa no 1, cidade universitária José da Silveira Neto. Guamá, Belém, PA - CEP:66075110, Pará, Brazil; E-mails: elmavieira@hotmail.com, cecysilva@gmail.com

Cite as: de Figueiredo Barros T, Takeuchi E, Souza C, Silva A, Melo Alencar C, Silva C. Marginal Degradation of Universal Adhesive Restorations in NCCLs: A Systematic Review and Meta-analysis. Open Dent J, 2024; 18: e18742106334186. <http://dx.doi.org/10.2174/0118742106334186240906093559>



Received: June 28, 2024
Revised: August 13, 2024
Accepted: August 29, 2024
Published: ?? ??, 2024



Send Orders for Reprints to
reprints@benthamscience.net

1. INTRODUCTION

Achieving a durable adhesive interface with enamel and dentin is an essential prerequisite to ensure the clinical success and longevity of adhesive dental restoration [1, 2]. To evaluate the effectiveness of this adhesion, tooth substrates have to be tested both in laboratory studies, under ideal working conditions, and in clinical trials that, when conducted appropriately, provide stronger scientific evidence [3, 4].

Non-carious cervical lesions (NCCLs) are considered most suitable for testing the clinical performance of direct adhesive restorations [5] due to the general absence of macro-mechanical retention [6, 7] and the presence of margins in both enamel and dentin. These margins are often sclerosed, which hinders adhesive effectiveness due to their acid-resistant characteristics [8, 9]. Variables such as marginal degradation, marginal staining and retention are the main parameters used to measure the clinical success of different adhesive strategies in these lesions [3].

Dental adhesives currently in use can be categorized into etching and rinse, self-etching, or selective enamel etching. In etch-and-rinse systems, the smear layer is removed by applying orthophosphoric acid at a concentration of 30-40%, which exposes the collagen [10]. The resin is then applied, infiltrating the dentinal tubules and interweaving with the collagen fibers, creating a base for the hybrid layer upon polymerization [11]. Self-etch adhesives, on the other hand, use acidic monomers capable of demineralizing and penetrating the dentin without the need for rinsing [12]. These adhesives alter the smear layer and integrate it into the hybrid layer. However, the effectiveness of self-etch adhesives when bonding to enamel remains uncertain. To address this concern, it is suggested that the enamel margins of the cavity be roughened with orthophosphoric acid before applying moderately self-etch adhesives (selective enamel etching) [13]. The most recent generation of adhesive systems is the universal or multi-mode systems [14]. This nomenclature refers to the possibility of using these systems in several protocols (etch and rinse (ER), self-etching (SE), or selective enamel etching (SEE)), and it is up to the dental surgeon to decide which one is best suited for each clinical situation [14, 15]. Since their launch, several randomized clinical trials (RCTs) have been conducted to evaluate the clinical performance of these systems. Some studies have reported that the adhesive protocol used does not affect the clinical performance of restorations fabricated for NCCLs, especially with regard to the retention of the restorative material [15, 16]. However, others have reported that small marginal failures were three times more frequent when a universal adhesive was applied in the SE mode [17], that the adhesive strategy used affects the marginal staining of restorations [18], and that the clinical performance of these systems was better when the ER strategy was adopted [19].

The aim of this systematic review and meta-analysis was

to answer the following PICO question: can the adhesive protocols adopted in NCCLs restorations using a universal adhesive system influence the marginal degradation, marginal staining and retention of these restorations? The self-etching adhesive strategy and selective enamel etching were compared with the etch-and-rinse strategy as a control. Although meta-analyses with similar PICO questions have been published, they have presented contradictory results [20, 21]. This highlights the lack of consensus on the subject, which justifies the need for the present study. Moreover, the moderate certainty of evidence in the meta-analysis conducted by Uros *et al.* [21] suggests that future studies could have a significant impact and could alter the estimated effects.

2. MATERIALS AND METHODS

2.1. Protocol and Registration

The study protocol was registered with the Prospective Register of Systematic Reviews (PROSPERO; registration number: CRD42020200020) and adhered to the recommendations of the Preferred Reporting Items for Systematic Reviews and Meta-Analysis (PRISMA) [22].

2.2. Search Strategy

On July 15, 2022, six databases—PubMed, Web of Science, the Cochrane Central Register of Controlled Trials (CENTRAL), Scopus, Embase, and grey literature (OpenGrey)—were searched. Medical Subject Headings (MeSH) terms and keywords were utilized in the search strategies, which were adjusted accordingly for each database (Table 1). The search strategies were designed to find all relevant published articles without date restrictions or language. A supplementary manual search was also performed by reviewing the reference lists of the identified articles.

Eleven different universal adhesive systems were evaluated in the selected studies. The Single Bond Universal adhesive (3M ESPE) was employed in 13 studies [6-8, 16, 19, 29, 41, 42, 49, 51, 53, 55]. The other adhesives tested were Xeno Select (Dentsply) [45, 38], Prime&Bond Elect (Dentsply-Sirona) [29, 42, 45, 53], Gluma Bond Universal (Kulzer) [9], All Bond Universal (Bisco Dental) [9], Futurabond U (VOCO GmbH) [35-38, 46], Tetric N-Bond Universal (Ivoclar Vivadent) [44], Amber Universal (FGM) [43, 48], Adhese Universal (Ivoclar Vivadent) [40, 46, 47], Clearfil Universal Bond Quick (Kuraray Noritake) [50] and IBond Universal (Kulzer GmbH) [52].

The main restorative materials used were the Filtek Z350 XT (3M ESPE) composite resins [7, 8, 15, 16, 18, 19, 41, 49, 51, 55], Filtek Z250 (3M ESPE) [42], Evolux (Dentsply) [38, 45] Empress Direct (Ivoclar Vivadent) [44], Kalore (GC Corporation) [29, 53], Tetric EvoCeram (Ivoclar Vivadent) [37, 39, 40], Tetric N-Ceram (Ivoclar Vivadent) [43], Admira Fusion (Voco) [35-37, 47], Charisma Opal Flow (Haraeus-Kulzer) [6], Venus Diamond Flow (Kulzer GmbH) [52], G-aenial Universal Flo (GC Corporation) [6], Opalis (FGM) [48], and Liz (FGM) [43]. These were inserted in up to three increments. De Carvalho *et al.* [41] reported the layout sequence for each increment in the cavity.

Table 1. Search strategy in different databases.

Database	Search strategy
PubMed	<p>#1 (((((((((((((((((Tooth Abrasion[MeSH Terms]) OR (Dental Abrasion[Title/Abstract]) OR (Tooth Erosion[MeSH Terms]) OR (Tooth Erosion*[Title/Abstract]) OR (Tooth Attrition[MeSH Terms]) OR (Dental Attrition[Title/Abstract]) OR (Occlusal Wear[Title/Abstract]) OR (Tooth Cervix[MeSH Terms]) OR (Cementoenamel Junction[Title/Abstract]) OR (Cervix Dentis[Title/Abstract]) OR (CEJ[Title/Abstract]) OR (Tooth Wear[MeSH Terms]) OR (Tooth Wears[Title/Abstract]) OR (Dental Wear[Title/Abstract]) OR (class V[Title/Abstract]) OR (class 5[Title/Abstract]) OR (non-carious cervical lesion[Title/Abstract]) OR (non-carious lesion[Title/Abstract]) OR (noncarious cervical[Title/Abstract]) OR (NCCL[Title/Abstract])</p> <p>#2 (((((((((((Dentin-Bonding Agents[MeSH Terms]) OR (Acid Etching, Dental[MeSH Terms]) OR (Dental Etching[MeSH Terms]) OR (Universal adhesive[Title/Abstract]) OR (Adhesive System[Title/Abstract]) OR (Self adhesive[Title/Abstract]) OR (Self-adhesive[Title/Abstract]) OR (Self etch[Title/Abstract]) OR (Self-etch[Title/Abstract]) OR (Selective etch[Title/Abstract]) OR (Etching Modes[Title/Abstract])</p> <p>#3 (((((((Phosphoric Acids[MeSH Terms]) OR (Pyrophosphoric Acids[Title/Abstract]) OR (Universal adhesive[Title/Abstract]) OR (Etch-and-rinse[Title/Abstract]) OR (Total etch[Title/Abstract])</p> <p>#4 (((((((Dental Marginal Adaptation[MeSH Terms]) OR (Dental Marginal Adaptation*[Title/Abstract]) OR (Dental Restoration Failure[MeSH Terms]) OR (Dental Restoration Failure*[Title/Abstract]) OR (Dental Restoration Repair[MeSH Terms]) OR (Dental Restoration Repairs[Title/Abstract]) OR (Dentin Sensitivity[MeSH Terms]) OR (Dentin* Sensitivit*[Title/Abstract]) OR (Dentine Hypersensitivity[Title/Abstract]) OR (Tooth Sensitivit*[Title/Abstract]) OR (Dentin Hypersensitivity[Title/Abstract])</p> <p>#1 AND #2 AND #3 AND #4</p>
Web of Science	<p>#1 TS=(Tooth AND Abrasion) OR TS=(Dental AND Abrasion) OR TS=(Tooth AND Erosion) OR TS=(Tooth AND Erosion*) OR TS=(Tooth AND Attrition) OR TS=(Dental AND Attrition) OR TS=(Occlusal AND Wear) OR TS=(Tooth AND Cervix) OR TS=(Cementoenamel AND Junction) OR TS=(Cervix AND Dentis) OR TS=(CEJ) OR TS=(Tooth AND Wear) OR TS=(Tooth AND Wears) OR TS=(Dental AND Wear) OR TS=(class AND V) OR TS=(class 5) OR TS=(non-carious AND cervical AND lesion) OR TS=(non-carious AND lesion) OR TS=(noncarious AND cervical) OR TS=(NCCL)</p> <p>#2 TS=(Dentin-Bonding AND Agents) OR TS=(Acid AND Etching, AND Dental) OR TS=(Dental AND Etching) OR TS=(Universal AND adhesive) OR TS=(Adhesive AND System) OR TS=(Self AND adhesive) OR TS=(Self-adhesive) OR TS=(Self AND etch) OR TS=(Self-etch) OR TS=(Selective AND etch) OR TS=(Etching AND Modes)</p> <p>#3 TS=(Phosphoric AND Acids) OR TS=(Pyrophosphoric AND Acids) OR TS=(Universal AND adhesive) OR TS=(Etch-and-rinse) OR TS=(Etch AND rise) OR TS=(Total AND etch)</p> <p>#4 TS=(Dental AND Marginal AND Adaptation) OR TS=(Dental AND Marginal) OR TS=(Dental Restoration Failure) OR TS=(Dental AND Restoration AND Failure*) OR TS=(Dental AND Restoration AND Repair) OR TS=(Dental AND Restoration AND Repairs) OR TS=(Dentin AND Sensitivity) OR TS=(Dentin* AND Sensitivit*) OR TS=(Dentine AND Hypersensitivity) OR TS=(Tooth AND Sensitivit*) OR TS=(Dentin AND Hypersensitivity)</p> <p>#1 AND #2 AND #3 AND #4</p>
Cochrane	(Tooth Abrasion OR Dental Abrasion OR Tooth Erosion OR Tooth Erosion* OR Tooth Attrition OR Dental Attrition OR Occlusal Wear OR Tooth Cervix OR Cementoenamel Junction OR Cervix Dentis OR CEJ) OR Tooth Wear OR Tooth Wears OR Dental Wear OR class V OR class 5 OR non-carious cervical lesion OR non-carious lesion OR noncarious cervical OR NCCL) AND (Dentin-Bonding Agents OR Acid Etching, Dental OR Dental Etching OR Universal adhesive OR Adhesive System OR Self adhesive OR Self-adhesive OR Self etch OR Self-etch OR Selective etch OR Etching Modes) in Title Abstract Keyword AND (Phosphoric Acids OR Pyrophosphoric Acids OR Universal adhesive OR Etch-and-rinse OR Etch and rise OR Total etch) in Title Abstract Keyword AND (Dental Marginal Adaptation OR Dental Marginal Adaptation* OR Dental Restoration Failure OR Dental Restoration Failure* OR Dental Restoration Repair OR Dental Restoration Repairs OR Dentin Sensitivity OR Dentin* Sensitivit* OR Dentine Hypersensitivity OR Tooth Sensitivit* OR Dentin Hypersensitivity) in Title Abstract Keyword
Scopus	<p>#1 (TITLE-ABS-KEY (tooth AND abrasion) OR TITLE-ABS-KEY (dental AND abrasion) OR TITLE-ABS-KEY (tooth AND erosion) OR TITLE-ABS-KEY (tooth AND erosion*) OR TITLE-ABS-KEY (tooth AND attrition) OR TITLE-ABS-KEY (dental AND attrition) OR TITLE-ABS-KEY (occlusal AND wear) OR TITLE-ABS-KEY (cementoenamel AND junction) OR TITLE-ABS-KEY (cervix AND dentis) OR TITLE-ABS-KEY (cej) OR TITLE-ABS-KEY (tooth AND wear) OR TITLE-ABS-KEY (tooth AND wears) OR TITLE-ABS-KEY (dental AND wear) OR TITLE-ABS-KEY (class AND v) OR TITLE-ABS-KEY (class 5) OR TITLE-ABS-KEY (non-carious AND cervical AND lesion) OR TITLE-ABS-KEY (non-carious AND lesion) OR TITLE-ABS-KEY (noncarious AND cervical) OR TITLE-ABS-KEY (nccl))</p> <p>#2 (TITLE-ABS-KEY (dentin-bonding AND agents) OR TITLE-ABS-KEY (acid AND etching, AND dental) OR TITLE-ABS-KEY (dental AND etching) OR TITLE-ABS-KEY (universal AND adhesive) OR TITLE-ABS-KEY (adhesive AND system) OR TITLE-ABS-KEY (self AND adhesive) OR TITLE-ABS-KEY (self-etch) OR TITLE-ABS-KEY (selective AND etch) OR TITLE-ABS-KEY (etching AND modes))</p> <p>#3 (TITLE-ABS-KEY (phosphoric AND acids) OR TITLE-ABS-KEY (pyrophosphoric AND acids) OR TITLE-ABS-KEY (universal AND adhesive) OR TITLE-ABS-KEY (etch-and-rinse) OR TITLE-ABS-KEY (etch AND rise) OR TITLE-ABS-KEY (total AND etch))</p> <p>#4 (TITLE-ABS-KEY (dental AND marginal AND adaptation) OR TITLE-ABS-KEY (dental AND marginal AND adaptation*) OR TITLE-ABS-KEY (dental AND restoration AND failure) OR TITLE-ABS-KEY (dental AND restoration AND failure*) OR TITLE-ABS-KEY (dental AND restoration AND repair) OR TITLE-ABS-KEY (dental AND restoration AND repairs) OR TITLE-ABS-KEY (dentin AND sensitivity) OR TITLE-ABS-KEY (dentin* AND sensitivit*) OR TITLE-ABS-KEY (dentine AND hypersensitivity) OR TITLE-ABS-KEY (tooth AND sensitivit*) OR TITLE-ABS-KEY (dentin AND hypersensitivity))</p> <p>#1 AND #2 AND #3 AND #4</p>
OpenGrey	(Tooth Abrasion OR Dental Abrasion OR Tooth Erosion OR Tooth Erosion* OR Tooth Attrition OR Dental Attrition OR Occlusal Wear OR Tooth Cervix OR Cementoenamel Junction OR Cervix Dentis OR CEJ) OR Tooth Wear OR Tooth Wears OR Dental Wear OR class V OR class 5 OR non-carious cervical lesion OR non-carious lesion OR noncarious cervical OR NCCL) AND (Dentin-Bonding Agents OR Acid Etching, Dental OR Dental Etching OR Universal adhesive OR Adhesive System OR Self adhesive OR Self-adhesive OR Self etch OR Self-etch OR Selective etch OR Etching Modes) AND (Phosphoric Acids OR Pyrophosphoric Acids OR Universal adhesive OR Etch-and-rinse OR Etch and rise OR Total etch) AND (Dental Marginal Adaptation OR Dental Marginal Adaptation* OR Dental Restoration Failure OR Dental Restoration Failure* OR Dental Restoration Repair OR Dental Restoration Repairs OR Dentin Sensitivity OR Dentin* Sensitivit* OR Dentine Hypersensitivity OR Tooth Sensitivit* OR Dentin Hypersensitivity)

Database	Search strategy
Embase	Tooth abrasion':ti,ab,kw OR 'dental abrasion':ti,ab,kw OR 'tooth erosion':ti,ab,kw OR 'tooth erosion*':ti,ab,kw OR 'tooth attrition':ti,ab,kw OR 'dental attrition':ti,ab,kw OR 'occlusal wear':ti,ab,kw OR 'tooth cervix':ti,ab,kw OR 'cementoenamel junction':ti,ab,kw OR 'cervix dentis':ti,ab,kw OR 'cej':ti,ab,kw OR 'tooth wear':ti,ab,kw OR 'tooth wears':ti,ab,kw OR 'dental wear':ti,ab,kw OR 'class v':ti,ab,kw OR 'class 5':ti,ab,kw OR 'non-carious cervical lesion':ti,ab,kw OR 'non-carious lesion':ti,ab,kw OR 'noncarious cervical':ti,ab,kw OR 'nccl':ti,ab,kw) AND ('dentin-bonding agents':ti,ab,kw OR 'acid etching, dental':ti,ab,kw OR 'dental etching':ti,ab,kw OR 'universal adhesive':ti,ab,kw OR 'adhesive system':ti,ab,kw OR 'self adhesive':ti,ab,kw OR 'self etch':ti,ab,kw OR 'selective etch':ti,ab,kw OR 'etching modes':ti,ab,kw) AND (('phosphoric acids':ti,ab,kw OR 'pyrophosphoric acids':ti,ab,kw OR 'universal adhesive':ti,ab,kw OR 'etch and rinse':ti,ab,kw OR 'etch':ti,ab,kw) AND 'rise':ti,ab,kw OR 'total etch':ti,ab,kw)

2.3. Eligibility Criteria and Study Selection Process

Two researchers (EPV and TAFB) independently selected the titles and abstracts of the studies identified by searching the electronic databases and exported the data to EndNote (Clarivate Analytics, Philadelphia, USA). Duplicate studies were subsequently eliminated through a two-step process. Initially, EndNote software was employed to eliminate duplicates; however, due to variations in database indexing processes, this tool cannot eliminate all duplicates. Therefore, in the second step, articles were sorted alphabetically by title, and duplicate studies were identified and removed manually. Any differences of opinion among the researchers were resolved through discussion and consensus; if necessary, a third researcher (CMSS) was consulted. For studies that seemed to meet the exclusion criteria or lacked sufficient data in the title and abstract, the full-text article was obtained and reviewed to make a decision.

Inclusion criteria were established based on the following PICO strategy [23].

2.3.1. Patients

Adult patients presenting with NCCLs and with an indication for direct composite restoration. Lesions were required to be non-carious, non-retentive, more than 1 mm deep, involve both the enamel and dentin of vital, non-mobile teeth, and have the cavosurface margins involving not more than 50% of the enamel.

2.3.2. Intervention

Composite resin restorations performed using universal adhesive through selective enamel conditioning or self-etching adhesive strategies.

2.3.3. Comparison

Composite resin restorations performed using a universal adhesive through etch and rinse adhesive strategy.

2.3.4. Outcomes

Clinical signs of marginal degradation were considered as primary endpoints. Marginal staining and retention of the restoration as the secondary endpoints. Clinical assessments were based on the United States Public Health Service (USPHS) criteria and/or the World Dental Federation (FDI) criteria.

Only RCTs were considered. The reference lists of the RCTs that met all the inclusion criteria and were considered potentially relevant for this review were manually searched. Two researchers (EPV and TAFB) independently tracked all the references from these RCTs.

2.4. Risk of Bias

The full texts of articles that met the eligibility criteria were comprehensively and independently evaluated by two researchers (EPV and TAFB) for methodological bias risk using the Cochrane RoB 2 tool [24]. Disagreements were settled through discussion, with the involvement of a third researcher (CMSS) when required.

The overall risk of bias was rated as low, unclear, or high based on six key domains: bias arising from the randomization process; bias due to deviations from intended interventions; bias due to missing outcome data; bias in measurement of the outcome; bias in selection of the reported result; and overall. For all studies classified as "unclear" in a key domain, the authors of the article in question were contacted for additional information.

2.5. Data Overview

Two independent researchers (EPV and TAFB) extracted relevant study data from the eligible articles. Disagreements were resolved through discussion, and a third researcher (CMSS) was consulted when necessary.

Information about the author, year of publication, sample size, age of participants, study design, adhesive strategies used, commercial name and manufacturer of the universal adhesives, statistical analyses, follow-up period, and results regarding retention, marginal degradation and marginal staining were tabulated. In instances where data was missing, efforts were made to contact the corresponding author *via* email weekly for up to four weeks to obtain the necessary information.

2.6. Summary Measures and Summary of Results

The studies were categorized based on the criteria used for conducting the clinical assessments. The data collected were dichotomized (retention/non-retention, marginal degradation/no degradation, and marginal staining/no marginal staining) and analyzed using RevMan v 5.3 (The Cochrane Collaboration; Copenhagen, Denmark) by adopting the Mantel-Haenszel method, a random effects model, and with the risk difference as the effect measure.

Meta-analyses were performed for the variables retention, marginal degradation, and marginal staining to compare the adhesive strategies self-etching (SE) vs. etching and rinsing (ER) and selective enamel etching (SEE) vs. ER at different follow-up time points.

2.7. Grading the Certainty of Evidence

The certainty of evidence (certainty in effect estimates) was assessed by two independent reviewers (TAFB and

EVT) for the outcomes (retention, marginal degradation and marginal staining) using the GRADE classification. Any disagreements were resolved by discussion or consensus involving a third-party reviewer (AMS). The GRADE approach initially assumes that the included studies provide high-quality evidence. However, if serious or very serious problems related to the risk of bias, imprecision, inconsistency, indirectness, or publication bias are identified, the quality or certainty of the evidence is reduced accordingly to moderate, low, or very low [25, 26].

3. RESULTS

3.1. Study Selection

The initial search across all databases yielded 879 records. Out of these, 422 duplicate studies were eliminated using EndNote. Another 415 studies were removed after evaluation based on their titles and abstracts. Forty-two studies of interest were thoroughly read and analyzed in full-text form, and out of these, 29 met the pre-established inclusion criteria.

Among the articles excluded at this stage, seven did not adopt the conditioning and washing strategy [17, 27-31], which was adopted as a comparison parameter for study eligibility; the dentin was saturated with 100% ethanol prior to the application of the adhesive system in

one study [32-34]; and the dentin was pre-treated with an enzyme inhibitor (epigallocatechin-3-gallate) in another study [34]. Fig. (1) summarizes the article selection process according to the PRISMA statement.

3.2. Characterization of the Included Studies

The studies were characterized according to a pre-established data extraction protocol. A total of 800 participants were included in the studies (20-63 participants per study), and participant ages ranged from 20 to 84 years. In total, 3,621 NCCLs were restored (100-246 per study). The number of NCCLs ranged from 1 to 8 per participant. Twenty-one studies reported that the experimental design followed the established Consolidated Standards of Reporting Trials (CONSORT) guidelines [7, 8, 15, 16, 35-51]. Fifteen studies reported registering the clinical trial with the German Clinical Trials Register [52], ClinicalTrials.gov [35-37, 44, 46, 47, 50], or ReBEC [16, 38, 42, 43, 45, 48, 49]. Eighteen studies featured the paired design [6, 7, 16, 18, 19, 35-41, 44, 45, 48, 49].

The morphological characterization of the NCCLs was described in detail in 18 studies [19, 35-38, 41-45, 48, 49, 51, 29, 53]; this included information on their dimensions (cervical-incisal height, width, and depth) and the geometry (45°, 45-90°, 90-135°, >135o.) and degree of sclerosis according to the criteria described by Swift *et al.* [54]. Two studies [9, 50] reported the dimensions and

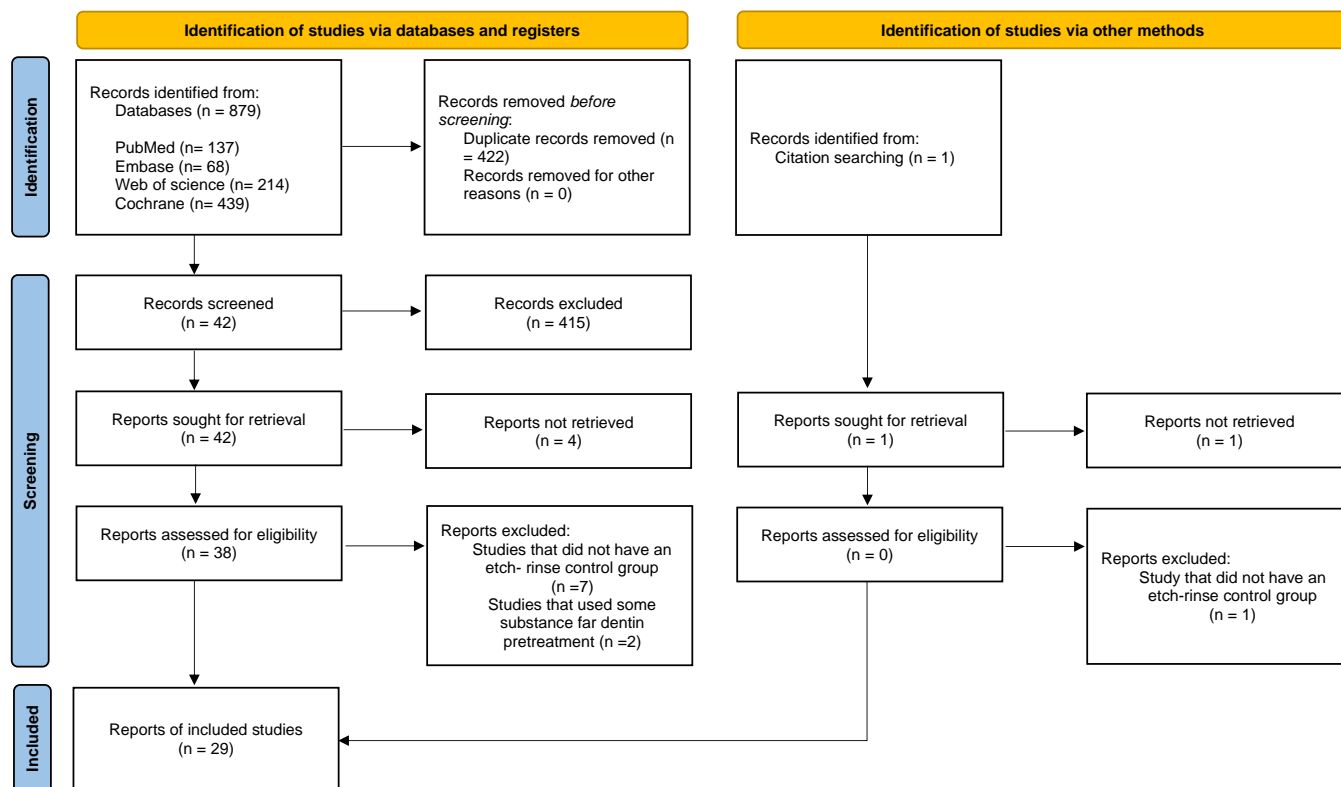


Fig. (1). Flowchart of the study selection process as recommended by the PRISMA statement (2020).

geometry of the NCCLs selected for sampling but did not report the degree of sclerosis present in them. Two studies [46, 47] described only the geometry and degree of sclerosis, while two others [8, 52] described only the depth of the lesions. Five studies did not describe any type of morphological characteristics of the NCCLs other than those that were part of the inclusion criteria [6, 18, 39, 40, 55].

The number of operators varied from study to study. In 12 studies, a single operator was responsible for performing all the restorations [8, 9, 29, 39, 40, 49, 50, 52, 55]. In the others, there were 2-5 operators who went through a calibration process. No operator was blinded to the adhesive strategies employed in any of the clinical trials, as each strategy required specific clinical procedures.

Twenty-five clinical trials described performing pumice and water prophylaxis immediately [6, 11, 12, 14, 19, 20, 23, 24, 31-33, 36, 40, 42, 56, 39-41, 43, 46, 47, 50, 52], one week [9], or two weeks [15, 16, 35-38, 44, 45, 49] before the restorative procedure. Only De Carvalho [41],

Oz *et al.* [9], Cruz *et al.* [40], Hass *et al.* [43], and Barceleiro *et al.* [38] reported that the participants received guidance on oral hygiene.

Sixteen clinical trials employed absolute isolation of the operative field for humidity control during the restorative procedure [15, 35-40, 42-45, 48, 49, 51]. Twelve trials used relative isolation techniques, such as the use of cotton rollers, retractor wire, and saliva suction [7-9, 19, 41, 56, 46, 47, 50, 52, 53]. One clinical trial described no humidity control procedure [6].

The mechanical treatment of the substrate also varied among the studies. Some trials did not prepare, roughen, or create any retention features on the enamel or dentin of the NCCL-affected teeth [15, 16, 38, 40, 42, 43, 45-49, 51]. Others employed hyper-mineralization of dentin by aspirating [29, 44, 53, 55] and/or creating bevels at the occlusal margin of the lesion [8, 18, 52, 55].

The USPHS or FDI criteria were used for the clinical evaluation of the restorations placed. The clinical follow-up periods ranged from 6 to 60 months. The main data extracted from the studies are summarized in Table 2.

Table 2. Characterization of the included studies

Study (Country, Year)	No. of Groups	Adhesive Strategy (n per group)	NCCL Preparation	Universal Adhesive (manufacturer)	Follow Up	Evaluation Criteria
Mena-Serrano <i>et al.</i> (Brazil/USA, 2012)	4	ER Moist Dentin (50) ER Dry Dentin (50) SE (50) SEE (50)	None	Single Bond Universal (3M ESPE)	6 months	USPHS
Perdigão <i>et al.</i> (Brazil/USA) 2014)					18 months	USPHS
Loguercio <i>et al.</i> (Brazil/ USA), 2015)					36 months	USPHS
Matos <i>et al.</i> (Brazil/ USA), 2020)					60 months	USPHS FDI
De Carvalho <i>et al.</i> (Brazil, 2015)	4	ER (38) SE (38) ER- Smokers (38) SE- No Smokers (38)	Not described	Single Bond Universal (3M ESPE)	12 months	USPHS
Lawson <i>et al.</i> (USA, 2015)	3	SU-ER (42) SU-SE (42) *SBM-ER (42)	0.5mm bevel on the occlusal margin	Single Bond Universal (3M ESPE) * Scotchbond™ Multipurpose - Step 3 (3M ESPE)	24 months	USPHS
Lopes <i>et al.</i> (Brazil, 2016)	4	ER Moist Dentin (31) ER Dry Dentin (31) SE (31) SEE (31)	None	XenoSelect, (Dentsply)	6 months	FDI
Barceleiro <i>et al.</i> (Brazil, 2022)					36 months	USPHS FDI
Albuquerque <i>et al.</i> (Brazil, 2017)	4	ER Moist Dentin (50) ER Dry Dentin (50) SE (50) SEE (50)	Not described	Futurabond U (VOCO)	6 months	FDI
Albuquerque <i>et al.</i> (Brazil, 2020)	-	-	-	-	18 months	USPHS FDI
Albuquerque <i>et al.</i> (Brazil, 2022)	-	-	-	-	36 months	USPHS FDI
Islatince <i>et al.</i> (Türkiye, 2018)	3	ER (82) SE (86) SEE (78)	Dentin roughening Bevel on enamel	Single Bond Universal (3M ESPE)	18 months	FDI
Loguercio <i>et al.</i> (Brazil/ Chile, 2018)	4	SU-ER (48) SU-SE (48) SU-ER + DR (48) SU-SE + DR (48)	Dentin roughening - DR (Half of NCCL)	Tetric N-Bond Universal (Ivoclar-Vivadent)	18 months	USPHS FDI

Study (Country, Year)	No. of Groups	Adhesive Strategy (n per group)	NCCL Preparation	Universal Adhesive (manufacturer)	Follow Up	Evaluation Criteria
Ruschel <i>et al</i> (Brazil/ USA, 2018)	4	SU-ER (52) SU-SE (50)	Dentin roughening	Single Bond Universal (3M ESPE) Prime & Bond Elect (Dentsply Sirona)	18 months	USPHS
Rushel <i>et al</i> (Brazil/ USA, 2019)		PBE-ER (50) PBE-SE (51)			36 months	USPHS
Matos <i>et al</i> (Brazil, 2019)	4	ER (54) SE (54)	None	Ambar Universal (FGM) Ambar Universal (FGM) + Nanoparticulas de Cu	18 months	USPHS modificado FDI
		ER + Cu (54) SE + Cu (54)				
Oz <i>et al</i> (Türkiye, 2019)	7	G-ER (21) G-SE (20) G-SEE (22)	Not described	Gluma Universal (Kulzer) All Bond Universal (Bisco) **Single Bond 2 (3M ESPE)	24 months	USPHS
		A-ER (20) A-SE (21) A-SEE (22)				
		**SB2-ER (29)				
Zanatta <i>et al</i> (Brazil, 2019)	4	SU-ER (38) SU-SE (38) SB2 (38) CLF (38)	None	Single Bond Universal (3M ESPE) Single Bond 2 (3M ESPE) Clearfill SE Bond (Kuraray Noritake Dental Inc.)	24 months	FDI
Atalay <i>et al</i> (Türkiye, 2019)	3	ER (55) SE (55) SEE (55)	0.5mm bevel (Occlusal margin)	Single Bond Universal (3M ESPE)	36 months	USPHS
Manarte-Monteiro (Portugal, 2019)	6	FBU-ER (35) FBU-SE (35) AD-ER (35) AD-SE (35) ***FBDC-SE (35) ***FBDC- SEE (35)	None	Futurabond U (VOCO) Adhese Universal (Ivoclar Vivadent) ***FuturaBond DC	12 months	FDI
Manarte-Monteiro (Portugal, 2022)	-	-	-	-	24 months	FDI
Cruz <i>et al</i> (Portugal, 2020)	2	ER (59) SE (58)	None	Tetric N-Bond Universal (Ivoclar-Vivadent)	6 months	FDI
Cruz <i>et al</i> (Portugal, 2021)	-	-	-	Adhese Universal (Ivoclar-Vivadent)	24 months	FDI
Kemaloglu <i>et al</i> (Türkiye, 2020)	4	ER + Charisma Opal Flow (25) SE + Charisma Opal Flow (25) ER + G-aenial Opal Flo (25) SE + G-aenial Opal Flo (25)	Not described	Single Bond Universal (3M ESPE)	24 months	USPHS
Perdigão <i>et al</i> (Spain/ USA, 2020)	4	SU-ER (34) SU-SE (35)	Not described	Single Bond Universal (3M ESPE) * Scotchbond™ Multiuso - Passo 3 (3M ESPE)	36 months	USPHS
		SU-ER + SBM* (34) SU-SE + SBM* (31)				
Hass <i>et al</i> (Brazil/ Chile, 2021)	4	ER+10s polymerization (35) ER+40s polymerization (35) SE+10s polymerization (35) SE+40s polymerization (35)	None	Ambar Universal (FGM)	18 months	FDI
Follak <i>et al</i> (Brazil, 2021)	4	PB-ER (53) PB-SE (50) SBU-ER (54) SBU-SE (54)	None	Prime&Bond Elect (Dentsply Sirona) Single Bond Universal (3M ESPE)	6 months	FDI USPHS
Merle <i>et al</i> (Germany, 2022)	4	iBond -ER (50) iBond-SE (50) iBond-SEE (29) ***OFL-ER (50)	Enamel and dentin roughening	iBond Universal (Kulzer GmbH) ***OptiBond FL (Kerr GmbH)	12 months	FDI

Study (Country, Year)	No. of Groups	Adhesive Strategy (n per group)	NCCL Preparation	Universal Adhesive (manufacturer)	Follow Up	Evaluation Criteria
Oz et al (Türkiye, 2022)	5	CUQ-ER (47) CUQ-SE (46) CUQ-SEE (47) C-SE (47) TNU-ER (47)	Not described	Clearfil Universal Bond Quick (Kuraray Noritake) Clearfil SE Bond (Kuraray Noritake) Tetric N-Bond Universal (Ivoclar Vivadent)	24 months	USPHS

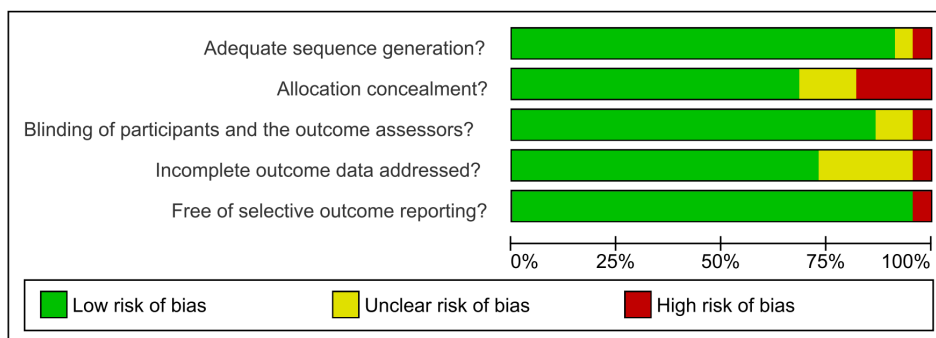
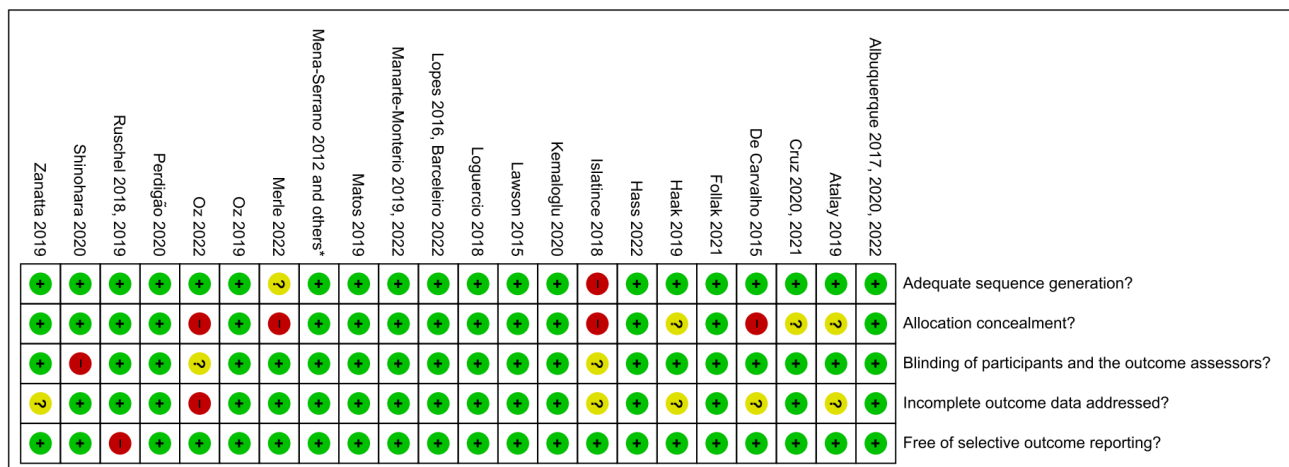


Fig. (2). Summary of risk of bias of included studies.

3.3. Analysis of the Risk of Bias in the Studies

Upon evaluating the predefined key domains to assess the risk of bias for each article, it was noted that none of the RCTs had implemented operator blinding. While the absence of operator blinding in RCTs indicates a significant risk of bias in this domain, we acknowledge that blinding might not have been feasible due to variations in clinical protocols for each restorative procedure. Evaluations for the other domains are detailed in Fig. (2).

3.4. Meta-analysis

3.4.1. Marginal Degradation

Figs. (3 and 4) illustrate the results of the meta-

analysis for the comparison of the SE and ER strategies. When using the USPHS criterion, the use of universal adhesives with the SE strategy resulted in the detection of clinical signs of marginal degradation at 12, 24, and 36 months of follow-up (Fig. 3). However, at 36 months, the collected data was characterized by high heterogeneity ($I^2= 79%$). When the FDI criteria were employed for evaluation, there was no difference in this regard between these strategies in the same follow-up period (Fig. 4).

There was no statistically significant difference between the SEE and ER strategies at 6, 12, 18, 24, and 36 months based on the USPHS criteria and at 6, 18, and 36 months based on the FDI criteria, as illustrated in Figs. (5 and 6), respectively.

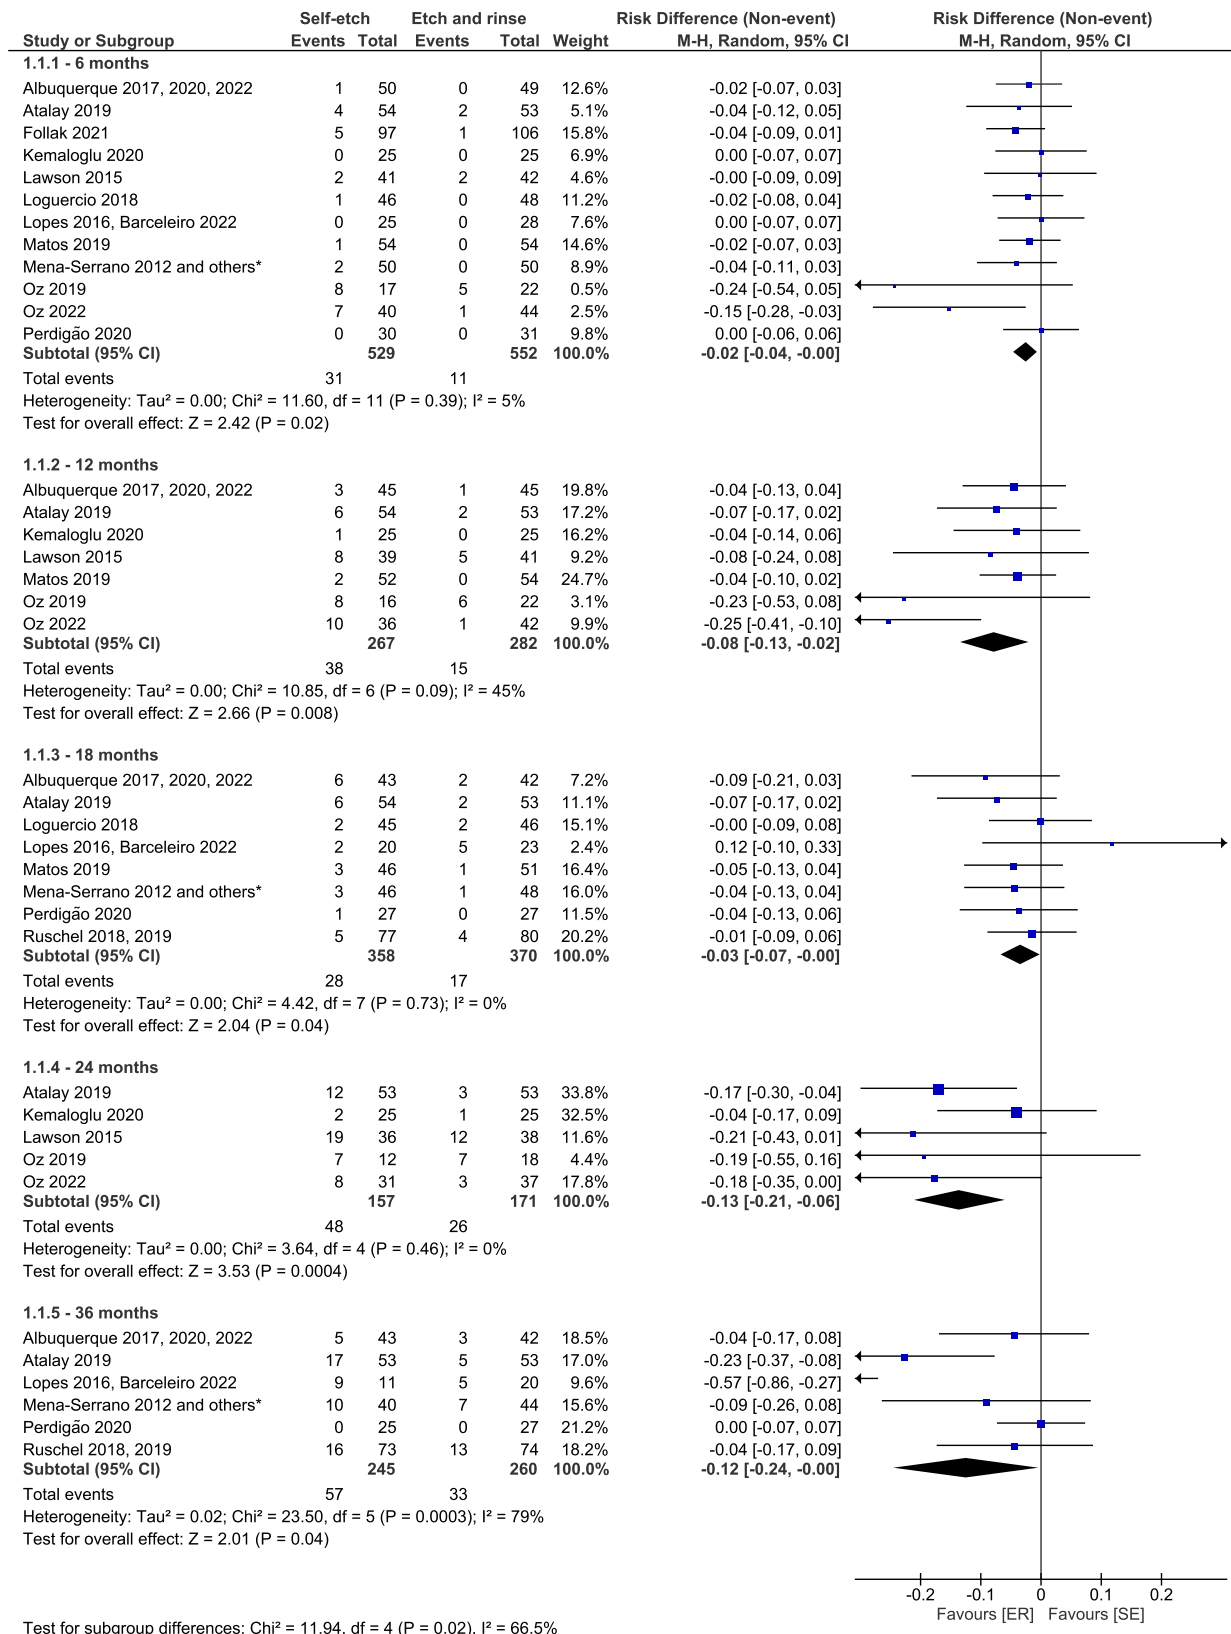


Fig. (3). Forest plot of the marginal degradation in the SE vs. ER strategies. Follow-ups 6, 12, 18, 24 and 36 months for USPHS criteria.

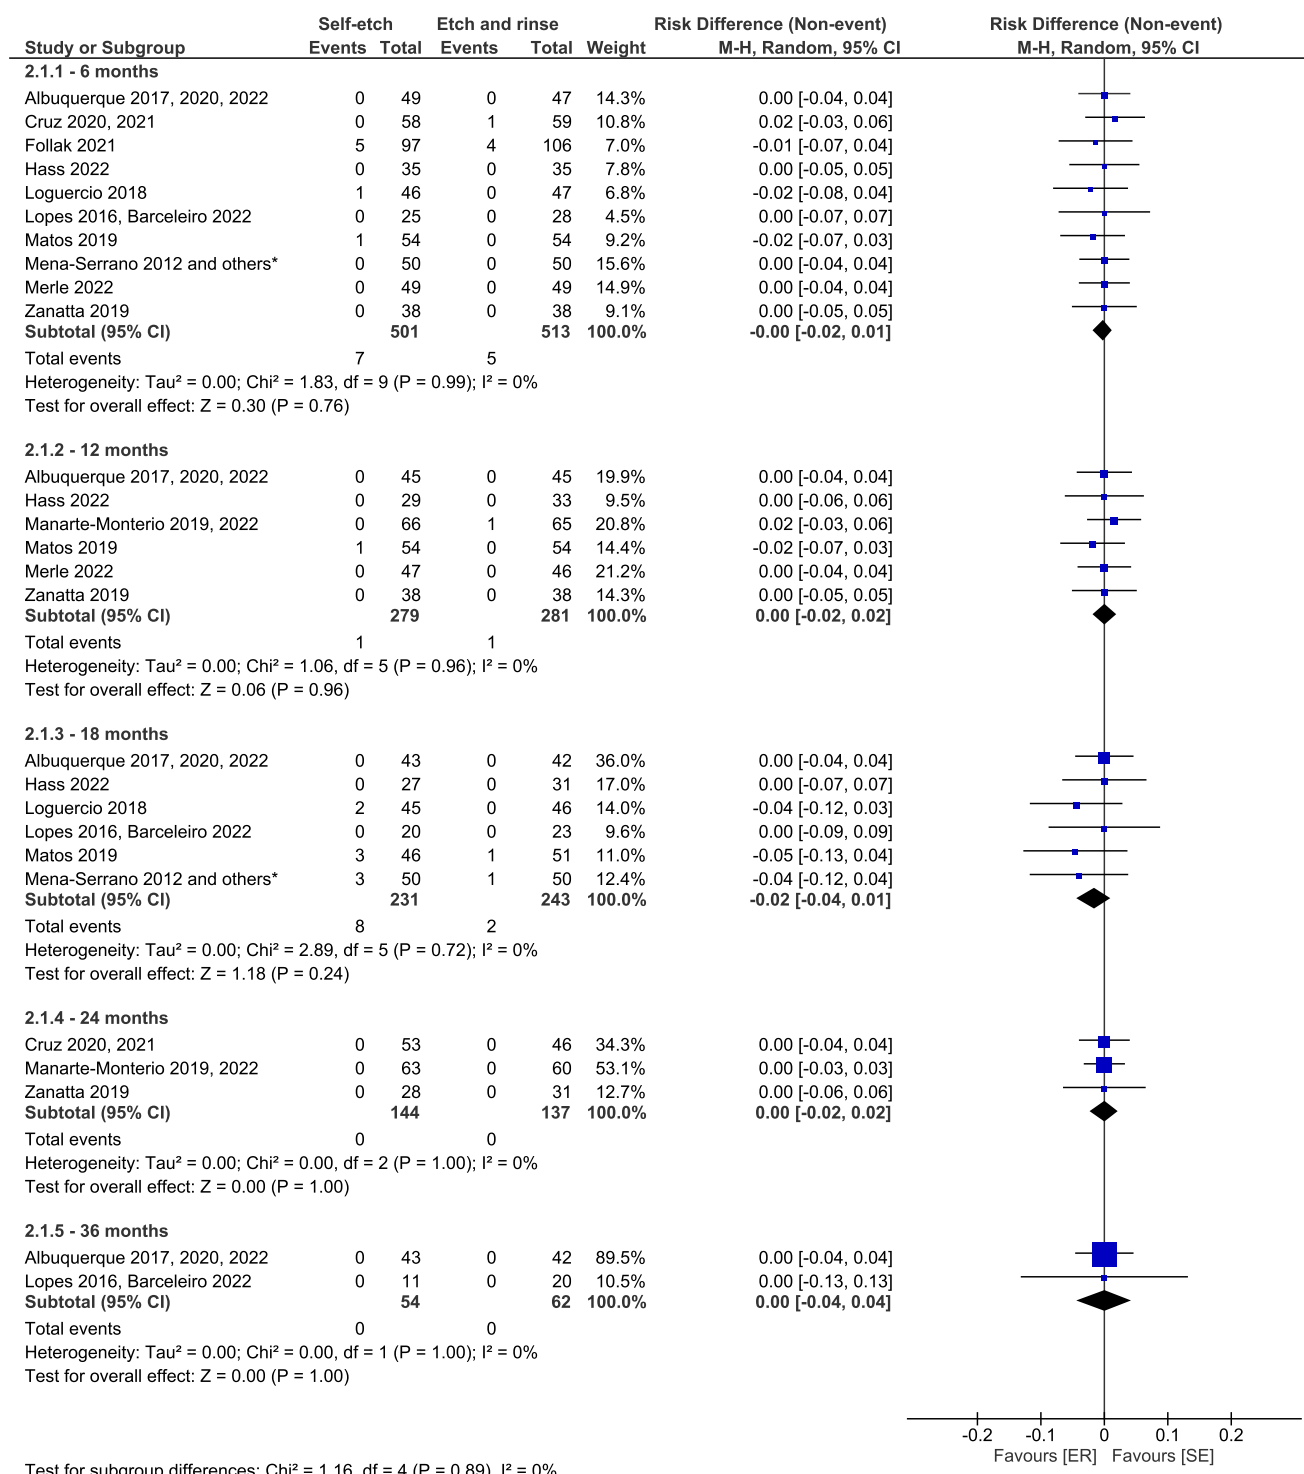


Fig. (4). Forest plot of the marginal degradation in the SE vs. ER strategies. Follow-ups 6, 12, 18, 24 and 36 months for FDI criteria.

3.4.2. Marginal Staining

Fig. (5) illustrates the results of the meta-analysis for the comparison of the SE and ER strategies. Employing the SE strategy resulted in the detection of clinical signs of marginal staining at 24 months of follow-up (Fig. 7)

with low data heterogeneity (I²=0%). When the FDI criteria were employed for evaluation, there was no difference in this regard between these strategies in the same follow-up period (Fig. 8).

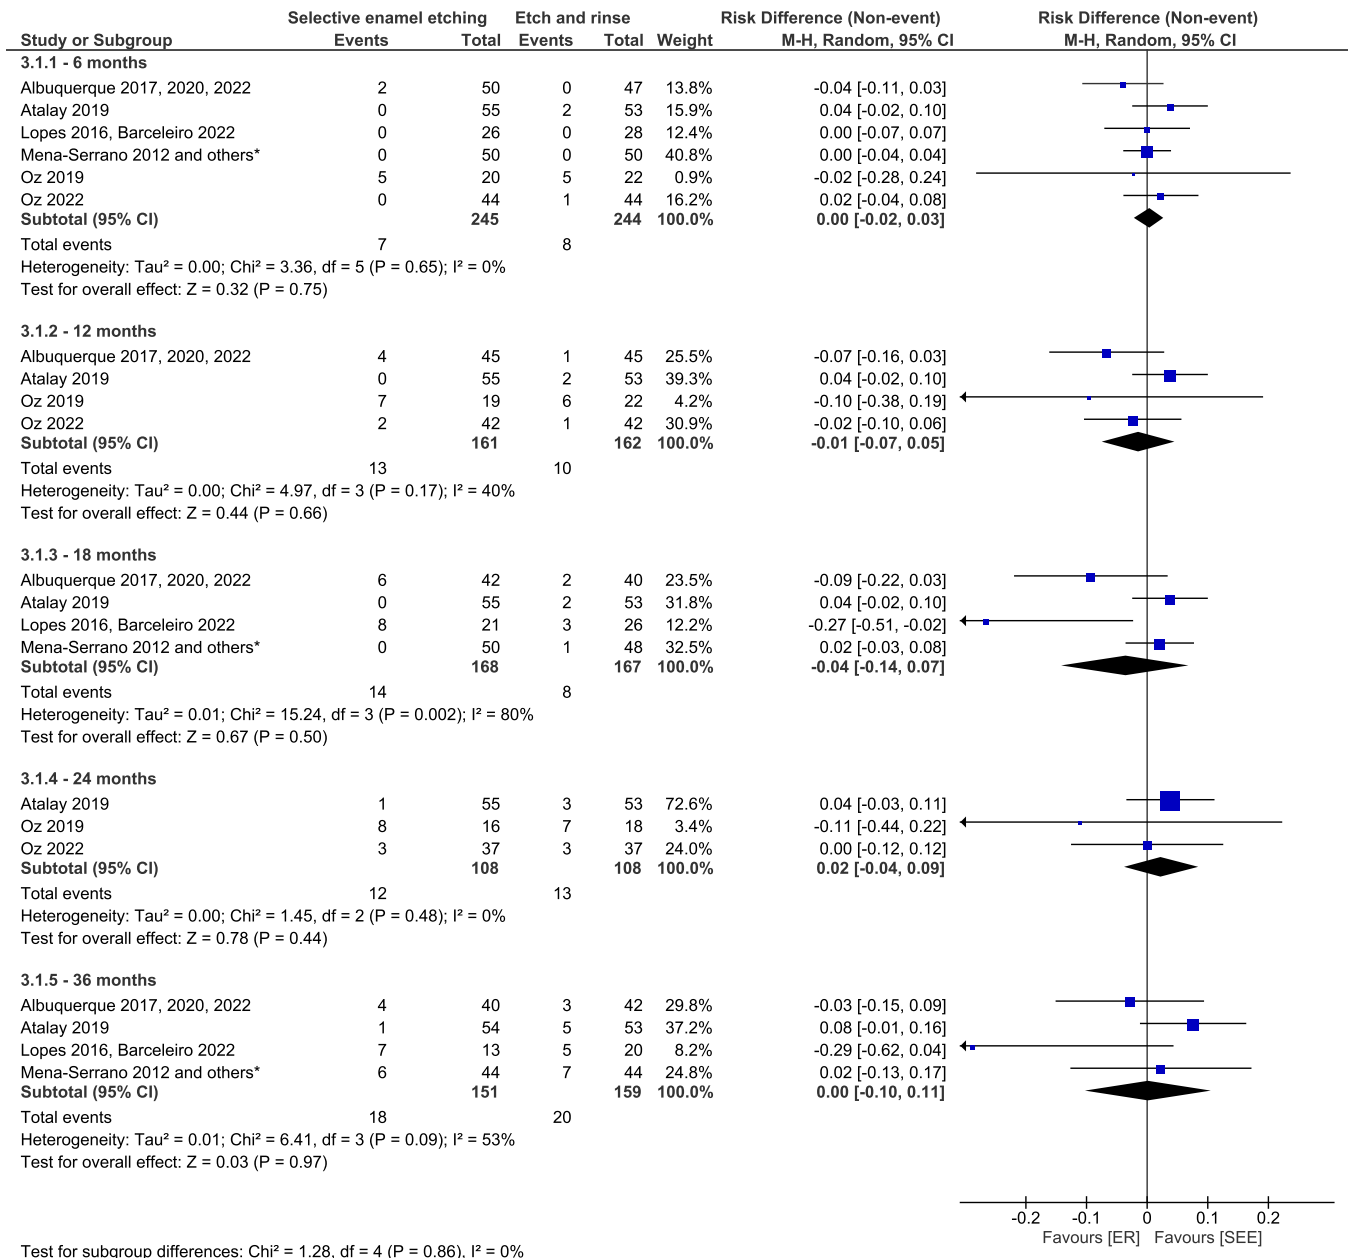


Fig. (5). Forest plot of the marginal degradation in the SEE vs. ER strategies. Follow-ups 6, 12, 18, 24 and 36 months for USPHS criteria.

There was no statistically significant difference between the SEE and ER strategies at 6, 12, 18, 24, and 36 months based on the USPHS criteria (Fig. 9), as well as at 6, 18, and 36 months based on the FDI criteria (Fig. 10).

3.4.3. Retention

The adhesive strategy adopted (ER, SE, or SEE) did not interfere with the retention of the restorative material in NCCLs over 36 months of clinical follow-up when a universal adhesive was used (Figs. 11, 12, 13 and 14) based on both the USPHS and FDI criteria.

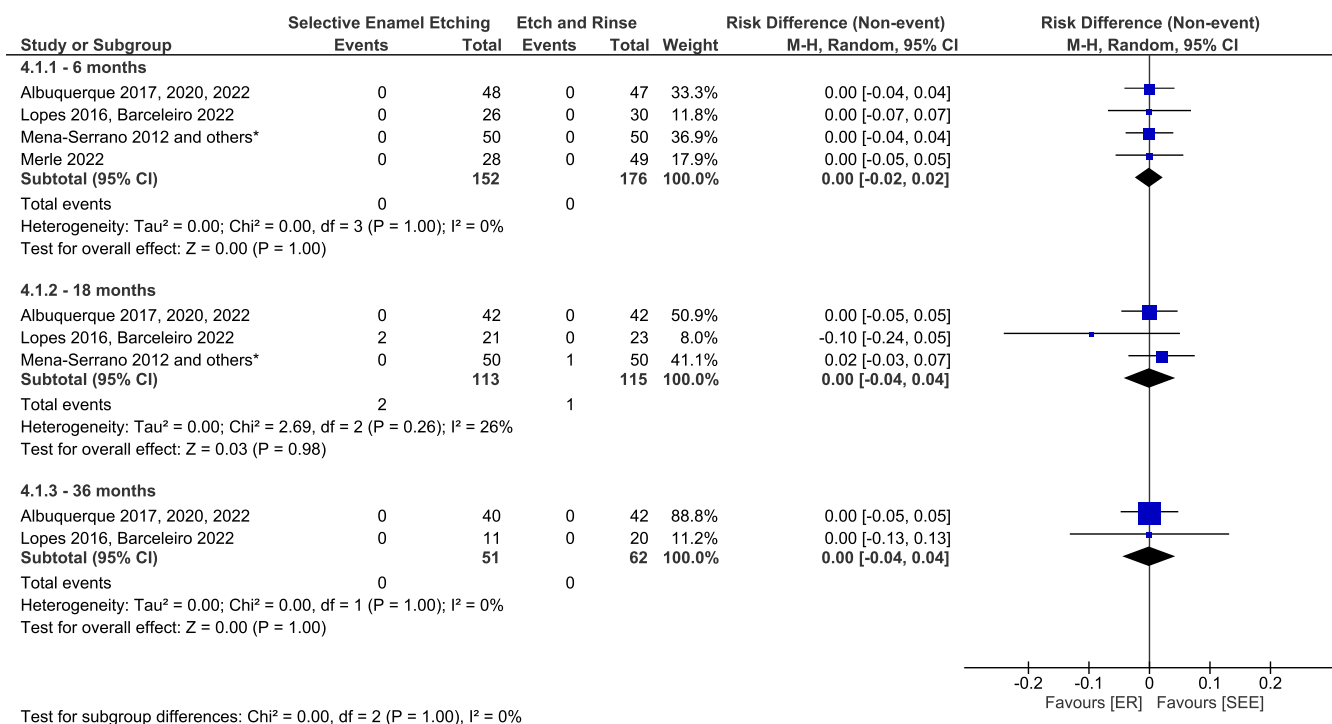
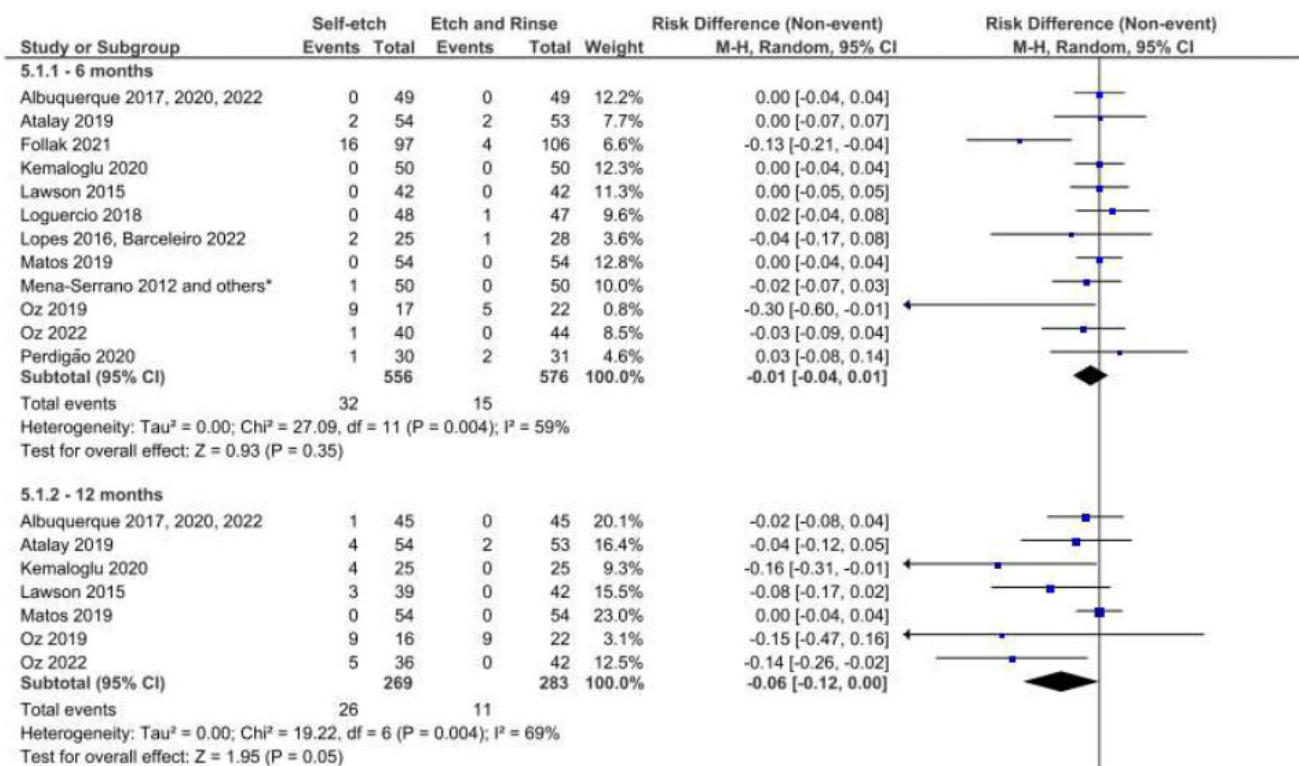


Fig. (6). Forest plot of the marginal degradation in the SEE vs. ER strategies. Follow-ups 6, 18 and 36 for FDI criteria.



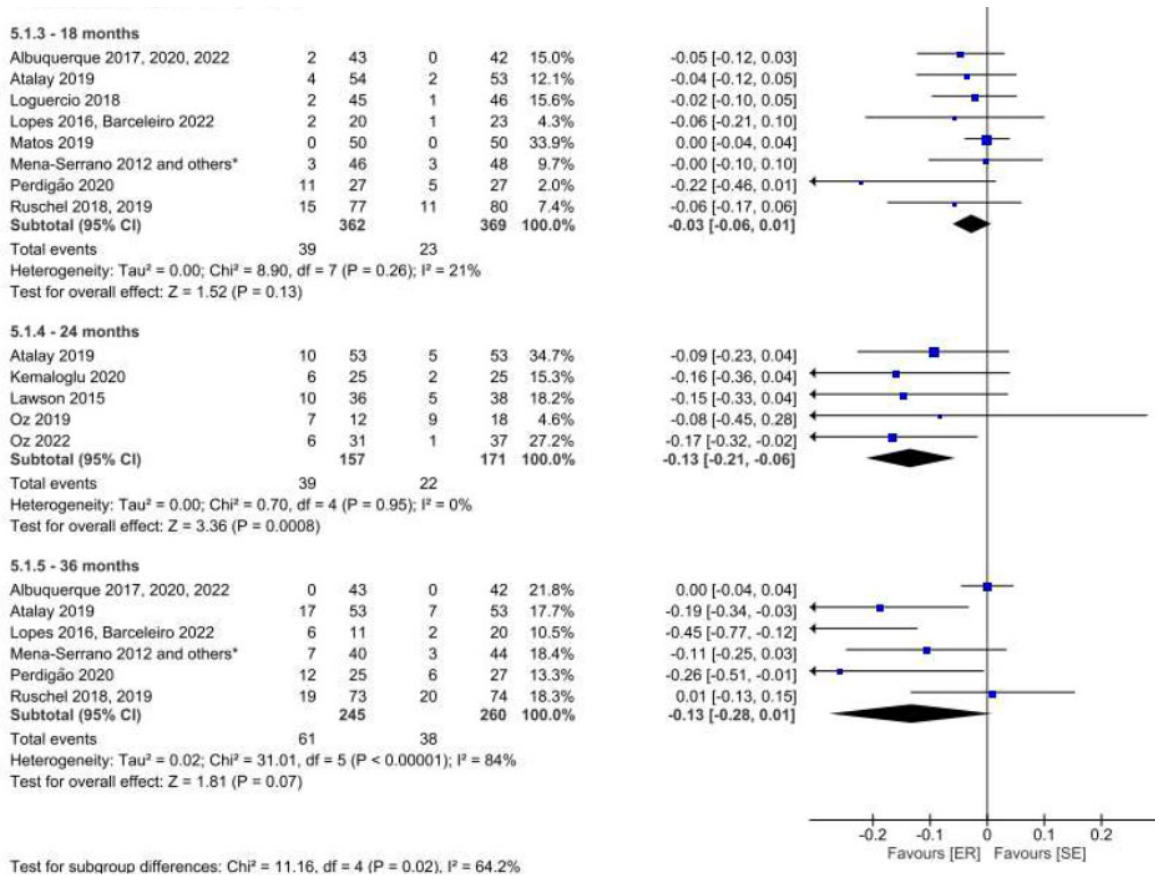
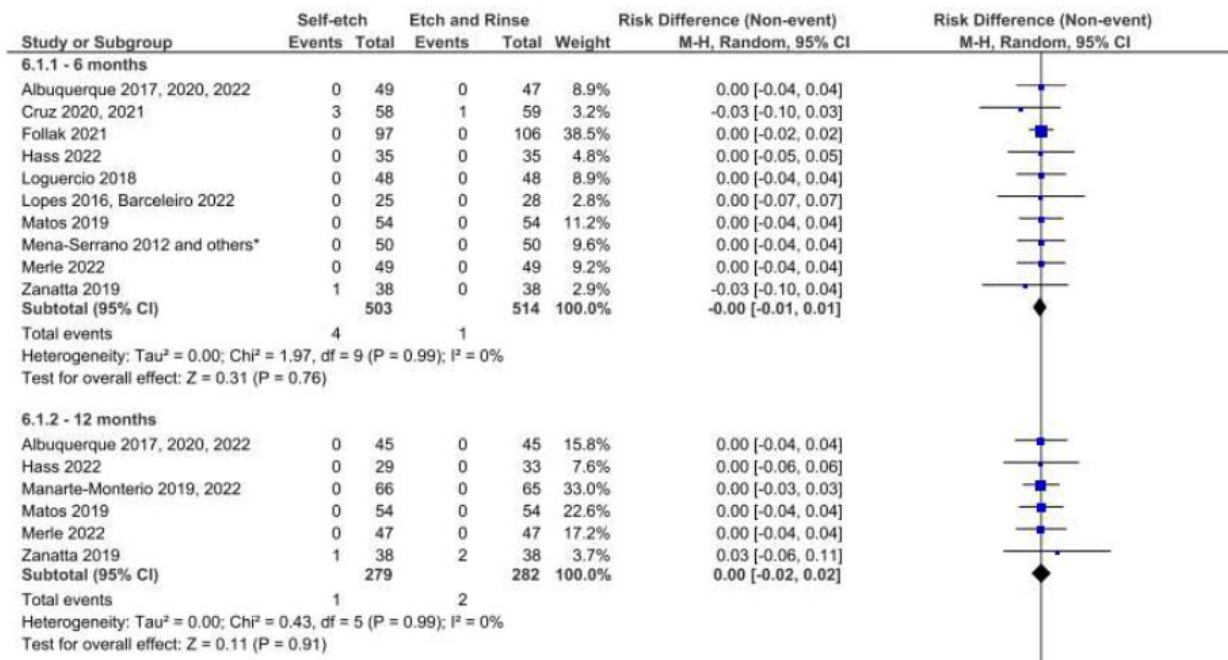


Fig. (7). Forest plot of the marginal staining in the SE vs. ER strategies. Follow-ups 6, 12, 18, 24 and 36 months for USPHS criteria.



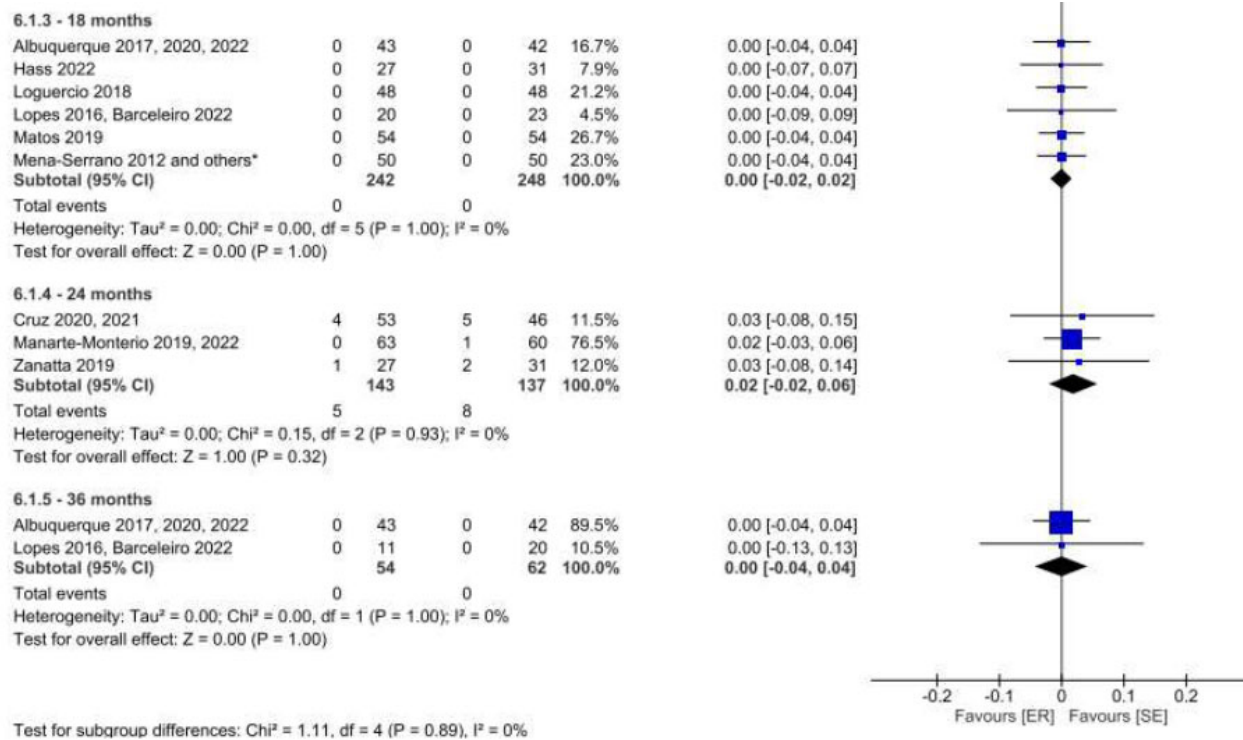
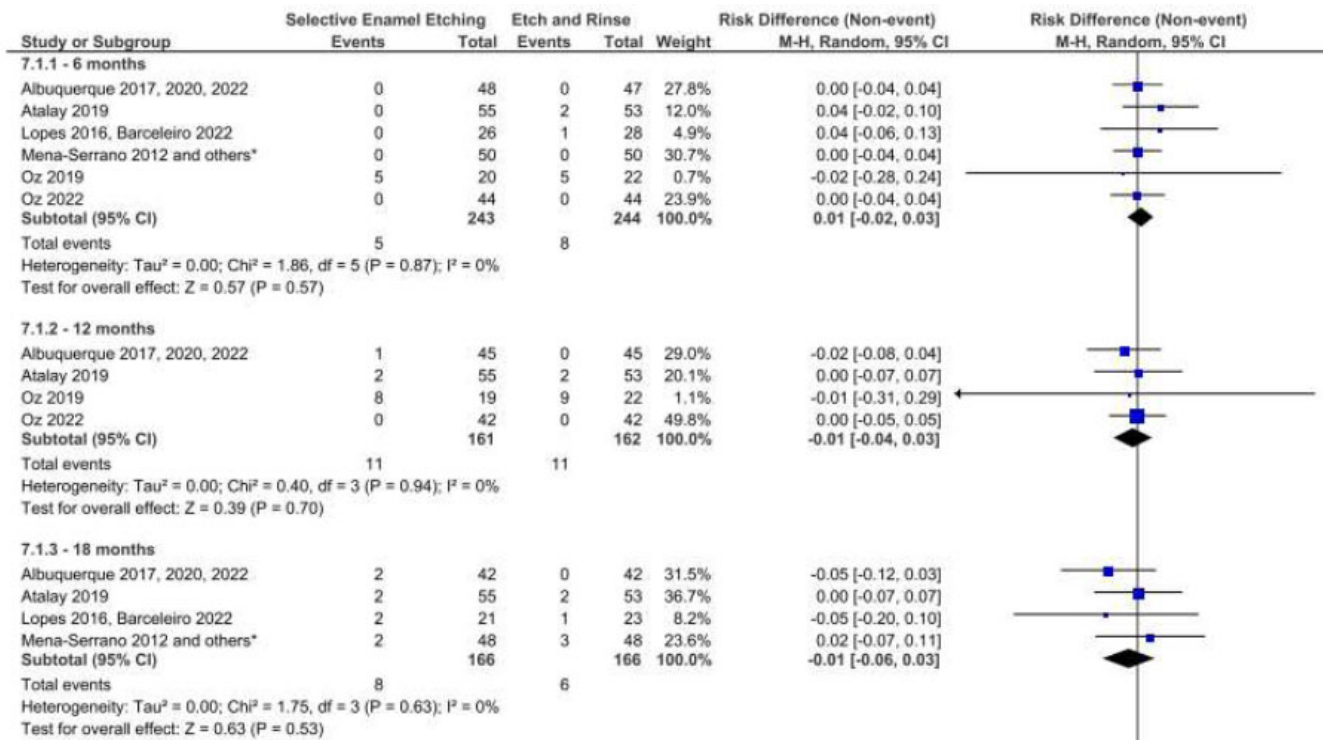


Fig. (8). Forest plot of the marginal staining in the SE vs. ER strategies. Follow-ups 6, 12, 18, 24 and 36 months for FDI criteria.



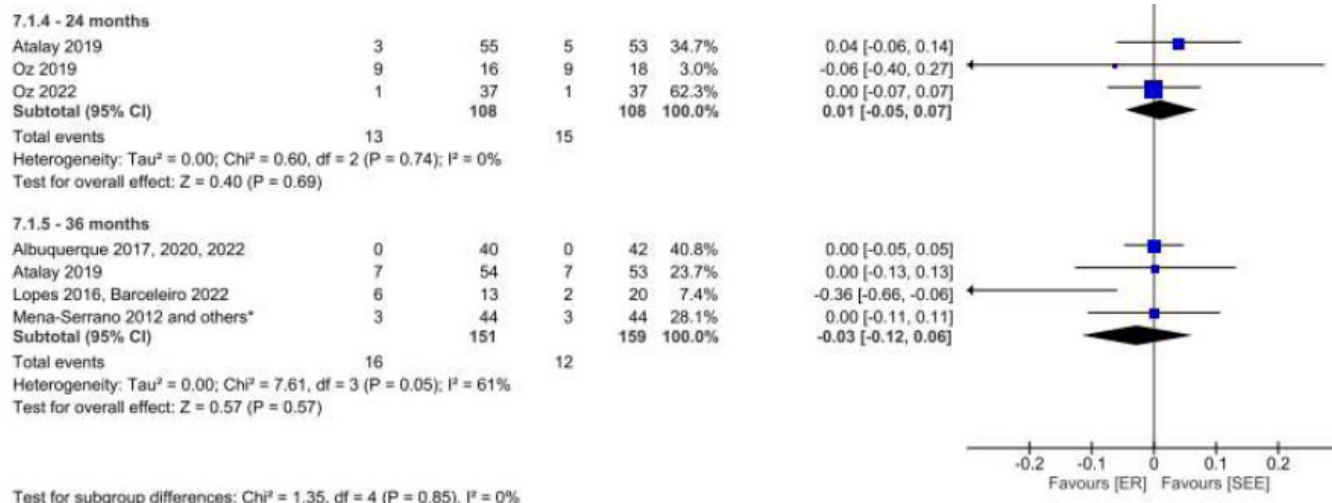


Fig. (9). Forest plot of the marginal staining in the SEE vs. ER strategies. Follow-ups 6, 12, 18, 24 and 36 months for USPHS criteria.

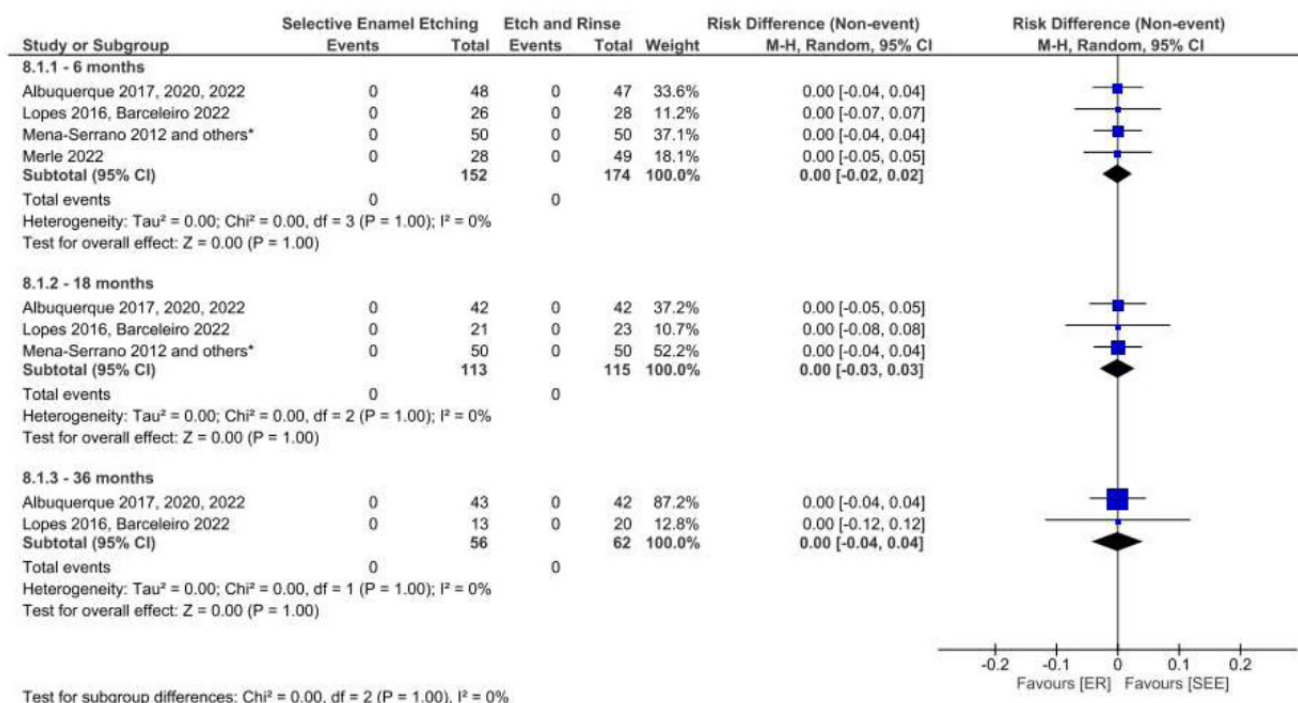


Fig. (10). Forest plot of the marginal staining in the SE vs. ER strategies. Follow-ups 6, 18 and 36 months for FDI criteria.

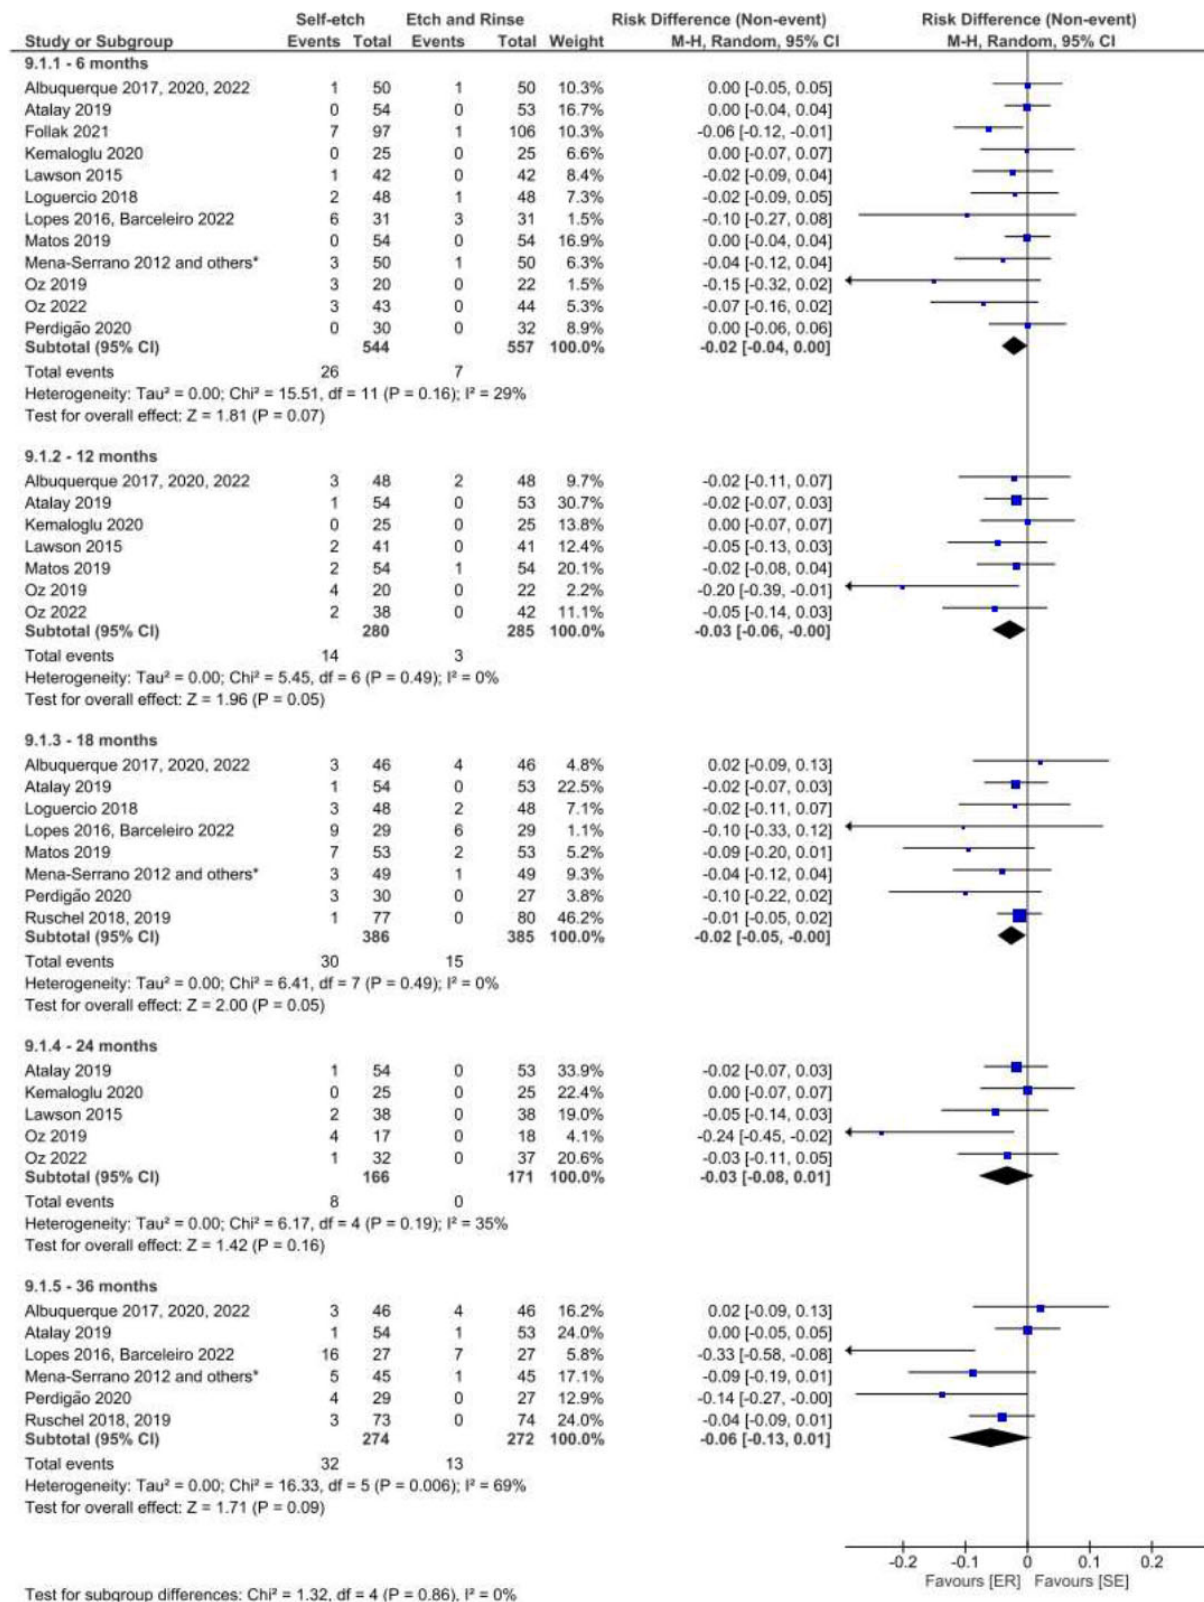


Fig. (11). Forest plot of the retention in the SE vs. ER strategies. Follow-ups 6, 12, 18, 24 and 36 months for USPHS criteria.

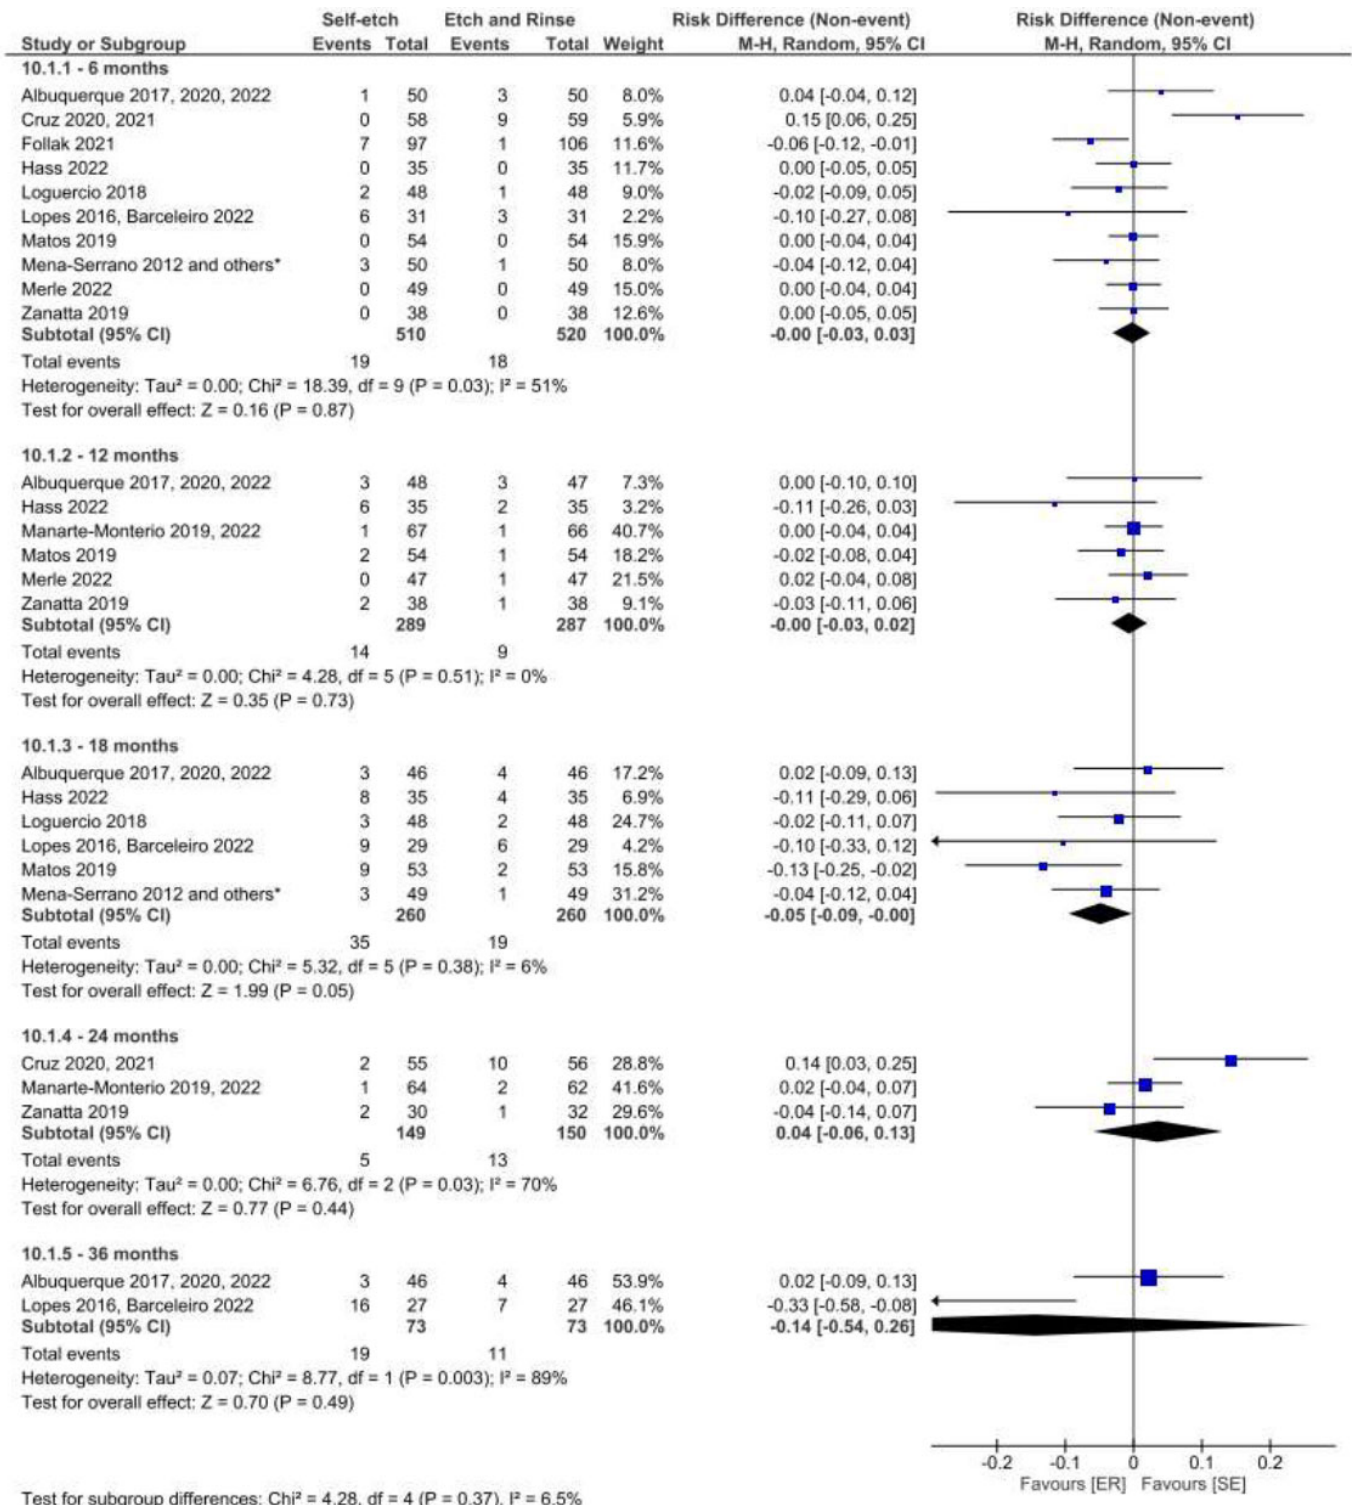


Fig. (12). Forest plot of the retention in the SE vs. ER strategies. Follow-ups 6, 12, 18, 24 and 36 months for FDI criteria.

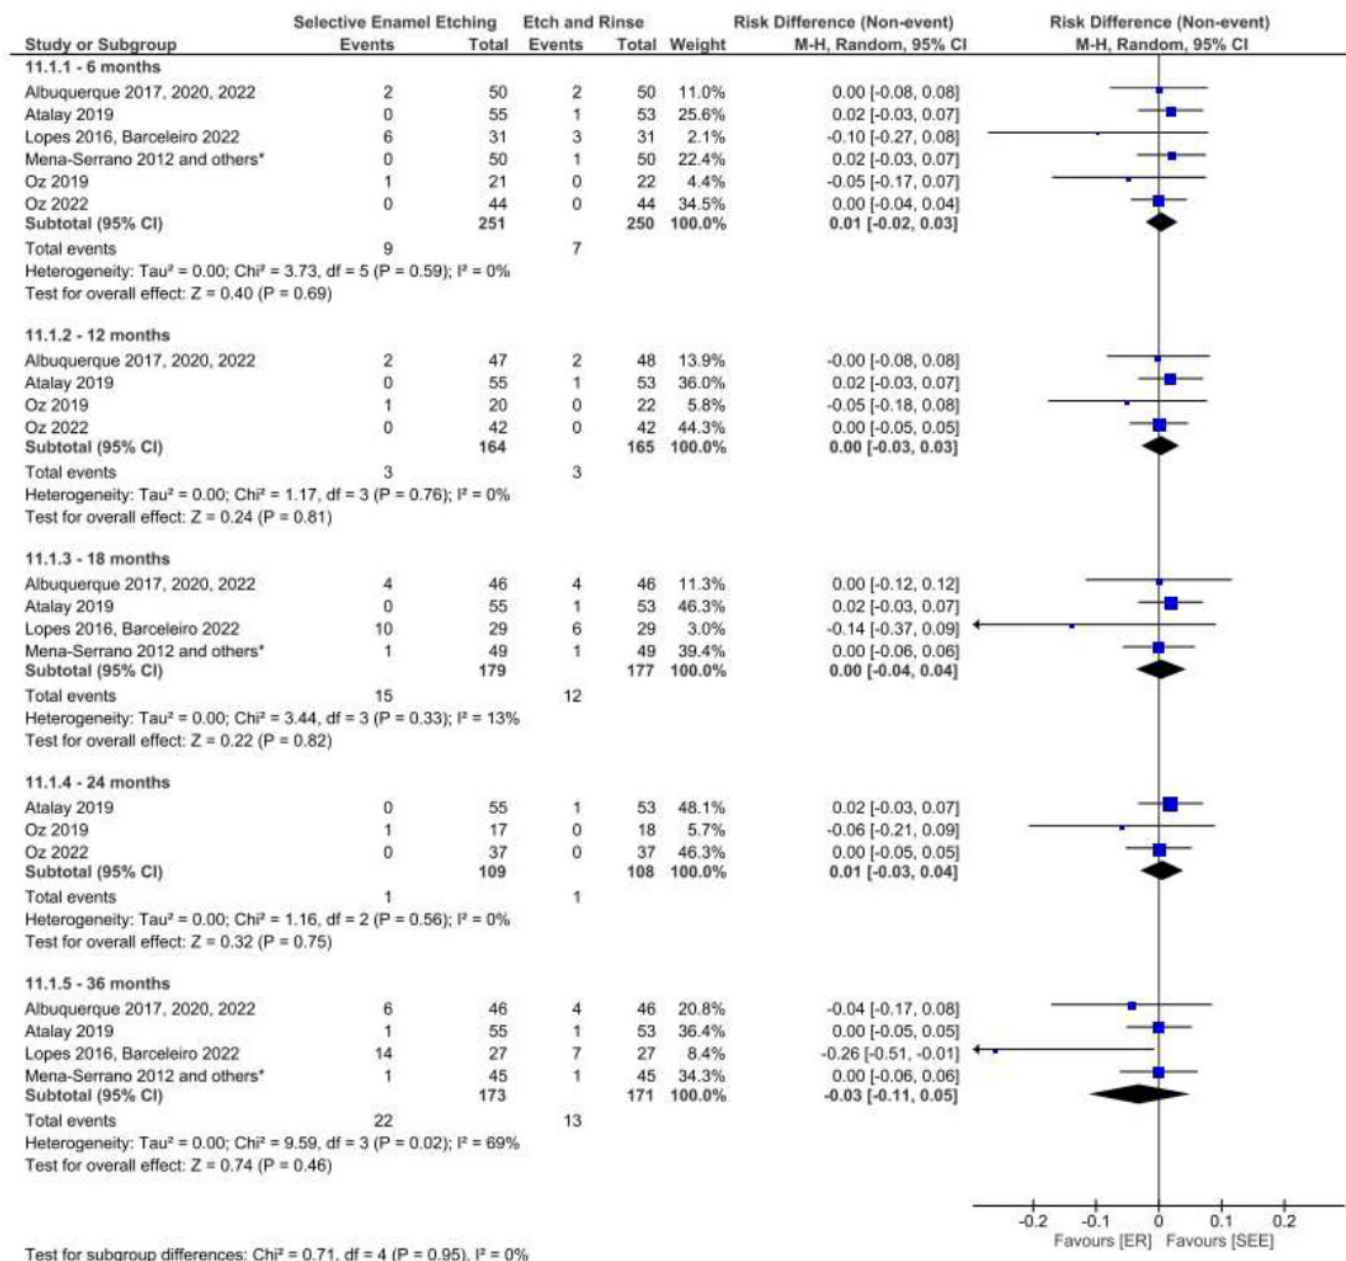


Fig. (13). Forest plot of the retention in the SEE vs. ER strategies. Follow-ups 6, 12, 18, 24 and 36 months for USPHS criteria.

3.5. Certainty of Evidence

3.5.2. Marginal Degradation and Marginal Staining - SE vs. ER Groups

Although a moderate certainty of evidence was observed for the marginal degradation data at the 12- and 24-month clinical follow-up when the USPHS criteria were

adopted, the certainty was very low at 36 months. The certainty of evidence regarding marginal staining data at 24 months was moderate. When the FDI criteria were adopted, the certainty of evidence was moderate for marginal degradation only at 12 months of clinical evaluation. For the other evaluation periods, the certainty of evidence was low for both degradation and marginal staining (Table 3).

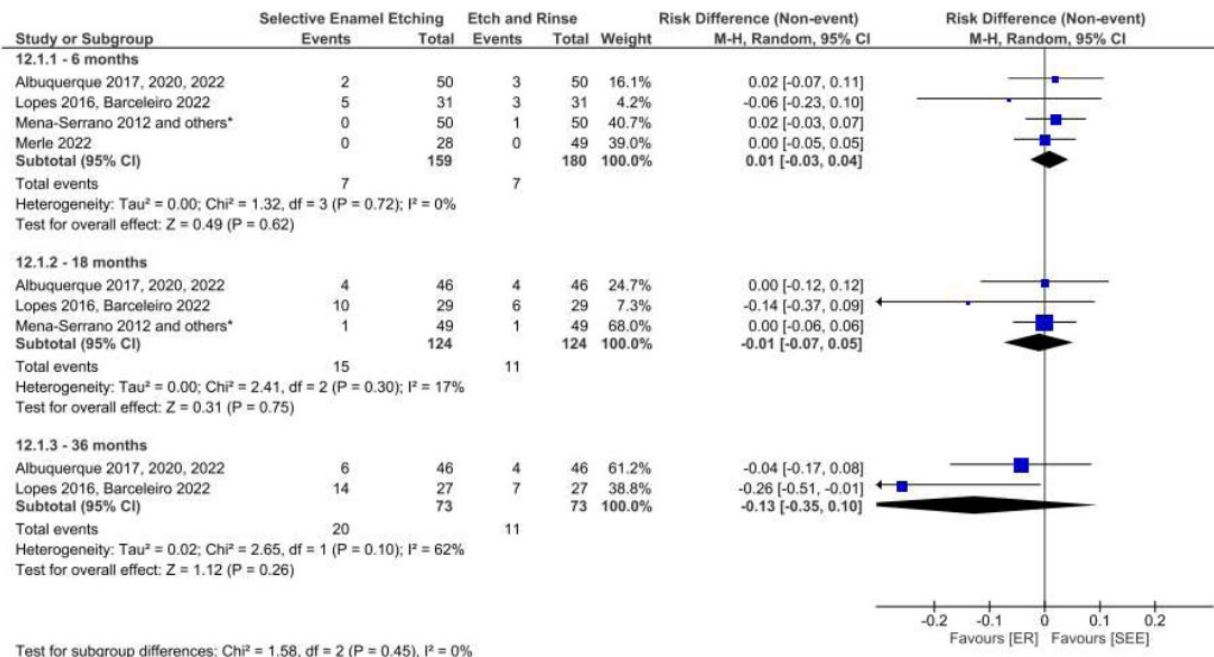


Fig. (14). Forest plot of the retention in the SEE vs. ER strategies. Follow-ups 6, 18 and 36 months for FDI criteria.

Table 3. Marginal degradation and marginal staining on SE strategy compared to ER (USPHS vs.FDI).

Criteria	Outcomes/Follow-up	No. of Participants (studies)/Follow-up	Certainty of the Evidence (GRADE)	Relative Effect (95% CI)	Anticipated Absolute Effects	
					Risk with Etch-and-rinse	Risk Difference with Self-etch
USPHS	Marginal degradation /12 months	549 (7 RCTs)	⊕⊕⊕○ Moderate ^a	RR 0.05 (0.01 to 0.10)	53 per 1.000	51 fewer per 1.000 (53 fewer to 48 fewer)
	Marginal degradation /24 months	328 (5 RCTs)	⊕⊕⊕○ Moderate ^a	RR 0.130 (0.040 to 0.022)	152 per 1.000	132 fewer per 1.000 (149 fewer to 146 fewer)
	Marginal degradation /36 months	505 (6 RCTs)	⊕○○○ Very low ^{a,b,c}	RR 0.08 (-0.04 to 0.20)	127 per 1.000	117 fewer per 1.000 (132 fewer to 102 fewer)
	Marginal staining /24 months	328 (5 RCTs)	⊕⊕⊕○ Moderate ^a	RR 0.12 (0.03 to 0.21)	129 per 1.000	113 fewer per 1.000 (125 fewer to 102 fewer)
FDI	Marginal degradation /12 months	560 (6 RCTs)	⊕⊕⊕○ Moderate ^a	RR 0.05 (0.01 to 0.10)	4 per 1.000	3 fewer per 1.000 (4 fewer to 3 fewer)
	Marginal degradation /24 months	281 (3 RCTs)	⊕⊕○○ Low ^{a,c}	RR 0.130 (0.040 to 0.022)	0 per 1.000	0 fewer per 1.000 (0 fewer to 0 fewer)
	Marginal degradation /36 months	116 (2 RCTs)	⊕⊕○○ Low ^{a,b,d}	RR 0.08 (-0.04 to 0.20)	0 per 1.000	0 fewer per 1.000 (0 fewer to 0 fewer)
	Marginal staining /24 months	280 (3 RCTs)	⊕⊕○○ Low ^{a,c}	RR 0.12 (0.03 to 0.21)	58 per 1.000	51 fewer per 1.000 (57 fewer to 46 fewer)

Note: CI: Confidence interval; RR: Risk ratio.

^a Most studies are at unclear risk of bias.

^b The confidence interval does not exclude great benefit or great harm, resulting in imprecision.

^c Imprecise estimates.

^d High and non-explained heterogeneity.

Table 4. Marginal degradation and marginal staining on SEE strategy compared to ER (USPHS vs.FDI).

Criteria	Outcomes/Follow-up	No. of Participants (studies)/Follow-up	Certainty of the Evidence (GRADE)	Relative Effect (95% CI)	Anticipated Absolute Effects	
					Risk with Etch-and-rinse	Risk Difference with Self-etch
U S P H S	Marginal degradation /6 months	489 (6 RCTs)	⊕⊕○○ Low ^{a,b}	RR -0.01 (-0.04 to 0.02)	33 per 1.000	33 fewer per 1.000 (34 fewer to 32 fewer)
	Marginal degradation /18 months	335 (4 RCTs)	⊕○○○ Very low ^{a,b,c}	RR -0.01 (-0.07 to 0.06)	48 per 1.000	48 fewer per 1.000 (51 fewer to 45 fewer)
	Marginal degradation /36 months	310 (4 RCTs)	⊕⊕○○ Low ^{a,d}	RR -0.06 (-0.14 to 0.01)	126 per 1.000	133 fewer per 1.000 (143 fewer to 125 fewer)
	Marginal degradation /6 months	487 (6 RCTs)	⊕⊕○○ Low ^{a,b}	RR -0.01 (-0.04 to 0.02)	33 per 1.000	33 fewer per 1.000 (34 fewer to 32 fewer)
	Marginal degradation /18 months	332 (4 RCTs)	⊕⊕○○ Low ^{a,b}	RR 0.01 (-0.03 to 0.06)	36 per 1.000	36 fewer per 1.000 (37 fewer to 34 fewer)
	Marginal staining /36 months	310 (4 RCTs)	⊕○○○ Very low ^{a,b,d}	RR 0.00 (-0.08 to 0.08)	75 per 1.000	75 fewer per 1.000 (82 fewer to 69 fewer)
F D I	Marginal degradation /6 months	328 (4 RCTs)	⊕⊕○○ Low ^{a,b}	RR -0.01 (-0.04 to 0.02)	0 per 1.000	0 fewer per 1.000 (0 fewer to 0 fewer)
	Marginal degradation /18 months	228 (3 RCTs)	⊕⊕○○ Low ^{a,b,c}	RR -0.01 (-0.07 to 0.06)	9 per 1.000	9 fewer per 1.000 (9 fewer to 8 fewer)
	Marginal degradation /36 months	113 (2 RCTs)	⊕⊕○○ Low ^{a,b,c}	RR -0.06 (-0.14 to 0.01)	0 per 1.000	0 fewer per 1.000 (0 fewer to 0 fewer)
	Marginal staining /6 months	326 (4 RCTs)	⊕⊕○○ Low ^{a,b}	RR -0.01 (-0.04 to 0.02)	0 per 1.000	0 fewer per 1.000 (0 fewer to 0 fewer)
	Marginal staining /18 months	228 (3 RCTs)	⊕⊕⊕○ Moderate ^{a,b}	RR 0.01 (-0.03 to 0.06)	0 per 1.000	0 fewer per 1.000 (0 fewer to 0 fewer)
	Marginal staining /36 months	118 (2 RCTs)	⊕⊕○○ Low ^{a,b,d}	RR 0.00 (-0.08 to 0.08)	0 per 1.000	0 fewer per 1.000 (0 fewer to 0 fewer)

Note: CI: Confidence interval; RR: Risk ratio.

^a Most studies are at unclear risk of bias.

^b The confidence interval does not exclude great benefit or great harm, resulting in imprecision.

^c Imprecise estimates.

^d High and non-explained heterogeneity.

3.5.3. Marginal Degradation and Marginal Staining - SEE vs. ER Groups

The certainty of the evidence was low or very low for all clinical evaluation periods when the SEE and ER strategies were compared for the degradation /marginal staining outcomes based on the USPHS criteria. Based on the FDI criteria, the certainty of evidence was moderate at 18 months for the marginal staining outcome and low for the other follow-up periods, both for degradation and marginal staining (Table 4).

3.5.4. Retention

When clinical evaluation was performed using the USPHS criteria, the certainty of evidence ranged from low to very low for all the different follow-up periods. When the FDI criteria were used, the certainty of evidence for the SE vs. ER comparison at 18 months, as well as the SEE

vs. ER comparison at 6 and 18 months, was moderate. For the other periods, the certainty of the evidence was low or very low. Table 5 summarizes the data for the different follow-up periods.

4. DISCUSSION

An increasing amount of research is being conducted to evaluate the clinical efficacy of universal adhesive systems. Generally, RCTs are conducted to assess clinical performance, with the retention of the restorative material being the main parameter used to evaluate longevity. Nevertheless, parameters such as marginal degradation and marginal staining are also crucial indicators for assessing the clinical success of adhesive procedures in NCCL restorations, despite the subjective nature of the evaluation criteria used (such as the USPHS and FDI criteria), which can result in considerable variability among evaluators [56].

Table 5. Retention on SE and SEE strategies compared to ER (USPHS vs. FDI).

Criteria	Strategy	Outcomes/Follow-up	No. of Participants (studies)	Certainty of the Evidence (GRADE)	Relative effect (95% CI)	Anticipated Absolute Effects	
						Risk with Etch-and-rinse	Risk Difference with Self-etch
USPHS	SE vs ER	Retention/6 months	1101 (12 RCTs)	⊕⊕○○ Low ^{a,b}	RR 0.01 (-0.01 to 0.03)	13 per 1.000	12 fewer per 1.000 (13 fewer to 12 fewer)
		Retention/12 months	565 (7 RCTs)	⊕⊕○○ Low ^{a,b}	RR 0.03 (-0.01 to 0.07)	11 per 1.000	10 fewer per 1.000 (11 fewer to 10 fewer)
		Retention/18 months	771 (8 RCTs)	⊕⊕○○ Low ^{a,d}	RR 0.02 (0.00 to 0.05)	39 per 1.000	38 fewer per 1.000 (39 fewer to 37 fewer)
		Retention/24 months	337 (5 RCTs)	⊕○○○ Very low ^{a,b,e}	RR 0.04 (-0.02 to 0.10)	0 per 1.000	0 fewer per 1.000 (0 fewer to 0 fewer)
		Retention/36 months	546 (6 RCTs)	⊕○○○ Very low ^{a,b,e}	RR 0.05 (-0.01 to 0.10)	48 per 1.000	45 fewer per 1.000 (48 fewer to 43 fewer)
	SEE vs ER	Retention/6 months	501 (6 RCTs)	⊕⊕○○ Low ^{a,b}	RR -0.01 (-0.05 to 0.02)	28 per 1.000	28 fewer per 1.000 (29 fewer to 27 fewer)
		Retention/18 months	356 (4 RCTs)	⊕⊕○○ Low ^{a,b}	RR -0.01 (-0.05 to 0.02)	68 per 1.000	68 fewer per 1.000 (71 fewer to 66 fewer)
		Retention/36 months	344 (4 RCTs)	⊕○○○ Very low ^{a,d}	RR 0.00 (-0.04 to 0.04)	76 per 1.000	76 fewer per 1.000 (79 fewer to 73 fewer)
	FDI	SE vs ER	Retention/6 months	1030 (10 RCTs)	⊕○○○ Very low ^{a,b,e}	RR 0.01 (-0.01 to 0.03)	35 per 1.000
Retention/12 months			576 (6 RCTs)	⊕⊕○○ Low ^{a,b}	RR 0.03 (-0.01 to 0.07)	31 per 1.000	30 fewer per 1.000 (32 fewer to 29 fewer)
Retention/18 months			520 (6 RCTs)	⊕⊕⊕○ Moderate ^{a,c}	RR 0.02 (0.00 to 0.05)	73 per 1.000	72 fewer per 1.000 (73 fewer to 69 fewer)
Retention/24 months			299 (3 RCTs)	⊕○○○ Very low ^{a,b,e}	RR 0.04 (-0.02 to 0.10)	87 per 1.000	83 fewer per 1.000 (88 fewer to 78 fewer)
Retention/36 months			146 (2 RCTs)	⊕⊕○○ Low ^{a,b,e}	RR 0.05 (-0.01 to 0.10)	151 per 1.000	143 fewer per 1.000 (152 fewer to 136 fewer)
SEE vs ER		Retention/ 6 months	339 (4 RCTs)	⊕○○○ Very low ^{a,b}	RR -0.01 (-0.05 to 0.02)	39 per 1.000	39 fewer per 1.000 (41 fewer to 38 fewer)
		Retention/ 18 months	248 (3 RCTs)	⊕⊕⊕○ Moderate ^{a,b}	RR -0.01 (-0.05 to 0.02)	121 per 1.000	122 fewer per 1.000 (127 fewer to 119 fewer)
		Retention/ 36 months	146 (2 RCTs)	⊕⊕○○ Low ^{a,b,e}	RR 0.00 (-0.04 to 0.04)	151 per 1.000	151 fewer per 1.000 (157 fewer to 145 fewer)

Note: CI: Confidence interval; RR: Risk ratio.

^a Most studies are at unclear risk of bias.

^b The confidence interval does not exclude great benefit or great harm, resulting in imprecision.

^c Imprecise estimates.

^d High and non-explained heterogeneity.

^e Moderate and non-explained heterogeneity.

Previously published systematic reviews have pointed out that when the substrate is dentin, the adhesive performance is largely pH-dependent [57, 58]. When an adhesive with a mild pH was used on dentin, the ER and SE adhesive strategies were found to be comparable [57]. However, the use of universal adhesives with intermediate strong pH resulted in a reduction in adhesive strength after aging, regardless of the substrate or adhesive strategy used [57]. These findings directed the authors of this meta-analysis to perform a sensitivity analysis for the

study by Oz *et al.* [9]. They chose to exclude data from groups that used the GLUMA® Bond Universal adhesive system (Kulzer; pH 1.6-1.8, intermediate strong), and considered only the data from the All Bond Universal adhesive (Bisco Dental; pH, 3.2), which resulted in the data becoming more homogeneous.

The quantitative analysis in the present study shows that the SE application mode influences marginal degradation and staining when compared to the ER strategy. Moreover, the results of the meta-analysis

indicate that the use of the SE adhesive strategy, as evaluated based on the USPHS clinical evaluation criteria, leads to clinical signs of marginal degradation at 12 and 24 months (moderate quality of evidence for both periods). At the 36-month follow-up, the ER strategy appeared to be superior to the SE strategy but with very low quality of evidence, which limits the confidence of the effect. Furthermore, these findings were not confirmed when the same comparison and follow-up periods were evaluated using the FDI criteria. Considering that both the USPHS and FDI criteria have been validated for assessing the clinical performance of restorations, this disagreement may be due to the difference in the number of studies that adopted these criteria (7 vs. 6 at 12 months; 5 vs. 3 at 24 months; and 6 vs. 2 at 36 months).

When marginal staining was the endpoint evaluated, the results of the meta-analysis showed that the ER strategy performed better than the SE strategy at 24 months of clinical follow-up, with moderate quality of evidence. Again, the same finding was not confirmed when the FDI criteria were employed. Despite the findings related to marginal degradation /staining, the adhesive strategy used (ER, SE, or SEE) did not have an impact on the retention of the restorative materials over 36 months based on both criteria. However, this result should be interpreted with some caution, since the quality of evidence was very low for this effect.

Our findings were contrary to those of the study by Arbildo *et al.* [59], where both the ER and SE strategies resulted in good adaptation and no marginal staining, but better retention results were observed when a universal adhesive was applied using the ER strategy. However, the authors combined data from clinical evaluations using both criteria (USPHS and FDI), as well as from different observation periods, in the same meta-analysis. Moreover, no tools for determining the quality of evidence were used.

More recently, Uros *et al.* [21] reported that the ER strategy showed better retention of restorations compared to the SE strategy at 12 months, but this difference was not observed after a longer period of clinical observation (36 months). However, the quality of evidence for the latter follow-up period was low. Fitting and marginal staining showed similar clinical characteristics for the comparison between the ER and SE strategies. In this study, separate meta-analyses were conducted for different clinical observation periods, although different clinical evaluation criteria (USPHS and FDI) were considered within each meta-analysis.

Dreweck *et al.* [60] conducted a network meta-analysis of 66 RCTs and concluded that none of the adhesive strategies compared showed superior clinical performance with regard to retention. A limitation of comparing this result with those of the present meta-analysis is that the previous study considered several types of adhesive systems, not just universal ones. However, the authors did raise a relevant point: the data related to clinical evaluation were grouped based on the evaluation period, as described in our methodology. As it is expected that the failure rates of these restorations will tend to increase

over the course of the clinical evaluation period, combining this data may result in the findings differing from the actual results.

A significant finding of this study was the notably high rates of marginal discoloration in restorations using universal adhesives in SE strategy. This was linked to the lower bonding effectiveness of self-etch adhesives on unetched enamel compared to etched enamel. NCCLs often involve sclerotic dentin, which can hinder optimal adhesion due to its resistance to acid [8, 9]. The self-etch mode might not be the best choice for surfaces that are highly sclerotic. Despite the drawbacks of ER, such as technical sensitivity and multiple steps, it tends to be more reliable than SE. Clinical studies have shown that SE results in higher rates of marginal discoloration than the ER strategy, which adversely affects the aesthetic outcome of restorations. Selective enamel etching appears to be a viable option to avoid acid etching of dentin without interfering with the clinical performance of restorations.

A limitation of this study is the high heterogeneity of some analyses due to high risk of bias and lack of information in some selected studies. More studies need to be conducted over longer evaluation periods before a more informed opinion can be provided regarding the results.

CONCLUSION

With moderate certainty of evidence, after 24 months of follow-up, the SE strategy results in the detection of clinical signs of marginal degradation and staining. However, at 36 months, these signs are only detectable with regard to marginal degradation, with very low certainty of evidence. Moreover, the adhesive strategy adopted (ER, SE, or SEE) does not influence the retention rate of restorations over 36 months of follow-up, although the quality of evidence in this regard ranged from low to very low.

CLINICAL RELEVANCE

The use of universal adhesive systems with the ER or SEE strategy promotes more predictable marginal degradation/staining results over longer periods of clinical observation.

AUTHORS' CONTRIBUTION

T.B., E.T., A.S., C.A., C.S.: Study conception and design; CS.:Data collection.

LIST OF ABBREVIATIONS

NCCLs	=	Non-cariou cervical lesions
RCTs	=	Randomized clinical trials
SE	=	Self-etching
USPHS	=	United States Public Health Service

CONSENT FOR PUBLICATION

Not applicable.

STANDARDS OF REPORTING

PRISMA guidelines and methodology were followed.

AVAILABILITY OF DATA AND MATERIAL

All data generated or analysed during this study are included in this published article.

FUNDING

None.

CONFLICT OF INTEREST

The authors declare no conflict of interest, financial or otherwise.

ACKNOWLEDGEMENTS

Declared none.

SUPPLEMENTARY MATERIAL

Supplementary material is available on the publisher's website along with the published article.

REFERENCES

- [1] Frankenberger R, Krämer N, Lohbauer U, Nikolaenko SA, Reich SM. Marginal integrity: Is the clinical performance of bonded restorations predictable *in vitro*? J Adhes Dent 2007; 9 (Suppl. 1): 107-16. PMID: 18341237
- [2] Frankenberger R, Lohbauer U, Roggendorf MJ, Naumann M, Taschner M. Selective enamel etching reconsidered: Better than etch-and-rinse and self-etch? J Adhes Dent 2008; 10(5): 339-44. PMID: 19058678
- [3] Peumans M, De Munck J, Mine A, Van Meerbeek B. Clinical effectiveness of contemporary adhesives for the restoration of non-carious cervical lesions. A systematic review. Dent Mater 2014; 30(10): 1089-103. <http://dx.doi.org/10.1016/j.dental.2014.07.007> PMID: 25091726
- [4] Reis A, Loguercio AD, Favoretto M, Chibinski AC. Some myths in dentin bonding: An evidence-based perspective. J Dent Res 2023; 102(4): 376-82. <http://dx.doi.org/10.1177/00220345221146714> PMID: 36707968
- [5] Araújo JF, Barros TAF, Braga EMF, Loretto SC, Silva e Souza PAR, Silva e Souza Júnior MH. One-year evaluation of a simplified ethanol-wet bonding technique: A randomized clinical trial. BDJ 2013; 24(3): 267-73.
- [6] Kemaloglu H, Atalayin Ozkaya C, Ergucu Z, Onal B. Follow-up of flowable resin composites performed with a universal adhesive system in non-carious cervical lesions: A randomized, controlled 24-month clinical trial. Am J Dent 2020; 33(1): 39-42. PMID: 32056414
- [7] Zanatta RF, Silva TM, Esper MALR, Bresciani E, Gonçalves SEP, Caneppele TMF. Bonding performance of simplified adhesive systems in non-carious cervical lesions at 2-year follow up: A double-blind randomized clinical trial. Oper Dent 2019; 44(5): 476-87. <http://dx.doi.org/10.2341/18-049-C> PMID: 30702405
- [8] Atalay C, Ozgunaltay G, Yazici AR. Thirty-six-month clinical evaluation of different adhesive strategies of a universal adhesive. Clin Oral Investig 2020; 24(4): 1569-78. <http://dx.doi.org/10.1007/s00784-019-03052-2> PMID: 31468262
- [9] Oz FD, Ergin E, Canatan S. Twenty-four-month clinical performance of different universal adhesives in etch-and-rinse, selective etching and self-etch application modes in NCCL - A randomized controlled clinical trial. J Appl Oral Sci 2019; 27: e20180358. <http://dx.doi.org/10.1590/1678-7757-2018-0358> PMID: 30994773
- [10] Yollar M, Karaoglanoglu S, Altiparmak ET, Aybala Oktay E, Aydin N, Ersoz B. The effects of dental adhesives total etch; self-etch and selective etch application procedures on microleakage in class II composite restorations. Eur Oral Res 2023; 57(3): 151-8. <http://dx.doi.org/10.26650/eor.20231197657> PMID: 37929222
- [11] Van Meerbeek B, Yoshihara K, Yoshida Y, Mine A, De Munck J, Van Landuyt KL. State of the art of self-etch adhesives. Dent Mater 2011; 27(1): 17-28. <http://dx.doi.org/10.1016/j.dental.2010.10.023>
- [12] Van Meerbeek B, Inoue S, Perdigão J, Lambrechts P, Vanherle G. Enamel and dentin adhesion. Carol Stream. (2nd ed.). Quintessence 2001; pp. 178-235.
- [13] Hickel R, Manhart J. Longevity of restorations in posterior teeth and reasons for failure. J Adhes Dent 2001; 3(1): 45-64. PMID: 11317384
- [14] Van Meerbeek B, Yoshihara K, Van Landuyt K, Yoshida Y, Peumans M. From Buonocore's pioneering acid-etch technique to self-adhering restoratives. A status perspective of rapidly advancing dental adhesive technology. J Adhes Dent 2020; 22(1): 7-34. PMID: 32030373
- [15] Loguercio AD, de Paula EA, Hass V, Luque-Martinez I, Reis A, Perdigão J. A new universal simplified adhesive: 36-Month randomized double-blind clinical trial. J Dent 2015; 43(9): 1083-92. <http://dx.doi.org/10.1016/j.jdent.2015.07.005> PMID: 26159382
- [16] Mena-Serrano A, Kose C, De Paula EA, et al. A new universal simplified adhesive: 6-month clinical evaluation. J Esthet Restor Dent 2013; 25(1): 55-69. <http://dx.doi.org/10.1111/jerd.12005> PMID: 23374411
- [17] Haak R, Hähnel M, Schneider H, et al. Clinical and OCT outcomes of a universal adhesive in a randomized clinical trial after 12 months. J Dent 2019; 90: 103200. <http://dx.doi.org/10.1016/j.jdent.2019.103200> PMID: 31562889
- [18] Lawson NC, Robles A, Fu CC, Lin CP, Sawlani K, Burgess JO. Two-year clinical trial of a universal adhesive in total-etch and self-etch mode in non-carious cervical lesions. J Dent 2015; 43(10): 1229-34. <http://dx.doi.org/10.1016/j.jdent.2015.07.009> PMID: 26231300
- [19] Perdigão J, Ceballos L, Giráldez I, Baracco B, Fuentes MV. Effect of a hydrophobic bonding resin on the 36-month performance of a universal adhesive—a randomized clinical trial. Clin Oral Investig 2020; 24(2): 765-76. <http://dx.doi.org/10.1007/s00784-019-02940-x> PMID: 31147827
- [20] Schroeder M, Correa IC, Bauer J, Loguercio AD, Reis A. Influence of adhesive strategy on clinical parameters in cervical restorations: A systematic review and meta-analysis. J Dent 2017; 62: 36-53. <http://dx.doi.org/10.1016/j.jdent.2017.05.006> PMID: 28495559
- [21] Josic Uros, Maravic Tatjana, Mazzitelli Claudia, et al. Is clinical behavior of composite restorations placed in non-carious cervical lesions influenced by the application mode of universal adhesives? A systematic review and meta-analysis. Dental Mater 2021; 37(11): e503-21. <http://dx.doi.org/10.1016/j.dental.2021.08.017>
- [22] Moher D, Liberati A, Tetzlaff J, Altman DG. Preferred reporting items for systematic reviews and meta-analyses: The PRISMA statement. Int J Surg 2010; 8(5): 336-41. <http://dx.doi.org/10.1016/j.ijsu.2010.02.007> PMID: 20171303
- [23] Maia LC, Antonio AG. Systematic reviews in dental research. A guideline. J Clin Pediatr Dent 2012; 37(2): 117-24. <http://dx.doi.org/10.17796/jcpd.37.2.h606137vj3826v61> PMID: 23534316
- [24] Higgins JPT, Savović J, Page MJ, Elbers RG, Sterne JAC. Chapter 8: Assessing risk of bias in a randomized trial. Cochrane Handbook for Systematic Reviews of Interventions version 62 . Cochrane 2021.
- [25] Cochrane handbook for systematic reviews of interventions. Oxford: The Cochrane Collaboration 2011.
- [26] Ryan R, Hill S. How to GRADE the quality of the evidence.

- Cochrane Consumers and Communication Group 2016.
- [27] Gonçalves DFM, Shinohara MS, Carvalho PRMA, *et al.* Three-year evaluation of different adhesion strategies in non-cariou cervical lesion restorations: A randomized clinical trial. *J Appl Oral Sci* 2021; 29: e20210192. <http://dx.doi.org/10.1590/1678-7757-2021-0192> PMID: 34705986
- [28] Oz FD, Kutuk ZB, Ozturk C, Soleimani R, Gurgan S. An 18-month clinical evaluation of three different universal adhesives used with a universal flowable composite resin in the restoration of non-cariou cervical lesions. *Clin Oral Investig* 2019; 23(3): 1443-52. <http://dx.doi.org/10.1007/s00784-018-2571-2> PMID: 30109443
- [29] Ruschel VC, Shibata S, Stolf SC, *et al.* Eighteen-month clinical study of universal adhesives in noncariou cervical lesions. *Oper Dent* 2018; 43(3): 241-9. <http://dx.doi.org/10.2341/16-320-C> PMID: 29676975
- [30] Rouse MA. Clinical evaluation of a universal adhesive in non-cariou cervical lesions. <http://dx.doi.org/10.7912/C2/1612>
- [31] Rouse MA, May JT, Platt JA, *et al.* Clinical evaluation of a universal adhesive in non-cariou cervical lesions. *J Esthet Restor Dent* 2020; 32(7): 691-8. <http://dx.doi.org/10.1111/jerd.12622> PMID: 32757232
- [32] Shinohara MS, Carvalho PRM, Neves Marcon L, Gonçalves DFM, Ramos FSE, Fagundes TC. Randomized clinical trial of different adhesion strategies in noncariou cervical lesion restorations: 1-year follow-up. *Quintessence Int* 2020; 51(5): 352-63. <http://dx.doi.org/10.3290/j.qi.a44367> PMID: 32253389
- [33] Souza MY. Use of the ethanol-wet dentin technique in dentin adhesion: *in vitro* influence of the smear layer, clinical evaluation with different adhesive protocols and systematic review. 2019. Available from: <http://hdl.handle.net/11449/183250>
- [34] Costa CAGA, Albuquerque NLG, Mendonça JS, Loguercio AD, Saboia VPA, Santiago SL. Catechin-based dentin pretreatment and the clinical performance of a universal adhesive: A two-year randomized clinical trial. *Oper Dent* 2020; 45(5): 473-83. <http://dx.doi.org/10.2341/19-088-C> PMID: 32352353
- [35] Albuquerque EG, Santana FWK, Calazans FS, *et al.* A new universal simplified adhesive: 6-month randomized multi-center clinical trial. *Rev Bras Odontol* 2017; 74(4): 251. <http://dx.doi.org/10.18363/rbo.v74n4.p.251>
- [36] de Albuquerque EG, Warol F, Calazans FS, *et al.* A new dual-cure universal simplified adhesive: 18-month randomized multicenter clinical trial. *Oper Dent* 2020; 45(5): E255-70. <http://dx.doi.org/10.2341/19-144-C> PMID: 33170938
- [37] de Albuquerque EG, Warol F, Tardem C, *et al.* Universal simplified adhesive applied under different bonding techniques: 36-month randomized multicentre clinical trial. *J Dent* 2022; 122: 104120. <http://dx.doi.org/10.1016/j.jdent.2022.104120> PMID: 35398450
- [38] Barceleiro MO, Lopes LS, Tardem C, *et al.* Thirty-six-month follow-up of cervical composite restorations placed with an MDP-free universal adhesive system using different adhesive protocols: A randomized clinical trial. *Clin Oral Investig* 2022; 26(6): 4337-50. <http://dx.doi.org/10.1007/s00784-022-04397-x> PMID: 35142923
- [39] Cruz J, Silva A, Eira R, Coito C, Lopes M, Cavalheiro A. 6-month clinical performance of a universal adhesive on non-cariou cervical lesions: self-etch and etch-and-rinse techniques. *Port J Stomatol Dent Maxillofac Surg* 2020; 61(3): 97-105. <http://dx.doi.org/10.24873/j.rpemd.2020.11.713>
- [40] Cruz J, Silva AL, Eira R, *et al.* 24-month clinical performance of a universal adhesive on non-cariou cervical lesions: Self-etch and etch-and-rinse techniques. *J Adhes Dent* 2021; 23(5): 379-87. <http://dx.doi.org/10.3290/j.jad.b2000173> PMID: 34549921
- [41] de Carvalho LD, Gondo R, Lopes GC. One-year clinical evaluation of resin composite restorations of noncariou cervical lesions in smokers. *J Adhes Dent* 2015; 17(5): 405-11. PMID: 26525004
- [42] Follak AC, Ilha BD, Oling J, Savian T, Rocha RO, Zovico FMS. Clinical behavior of universal adhesives in non-cariou cervical lesions: A randomized clinical trial. *J Dent* 2021; 113: 103747. <http://dx.doi.org/10.1016/j.jdent.2021.103747>
- [43] Hass V, Matos TP, Parreiras SO, *et al.* An 18-month clinical evaluation of prolonged polymerization of a universal adhesive in non-cariou cervical lesions: A double-blind randomized clinical trial. *Dent Mater* 2022; 38(1): 68-78. <http://dx.doi.org/10.1016/j.dental.2021.10.012> PMID: 34836700
- [44] Loguercio AD, Luque-Martinez IV, Fuentes S, Reis A, Muñoz MA. Effect of dentin roughness on the adhesive performance in non-cariou cervical lesions: A double-blind randomized clinical trial. *J Dent* 2018; 69: 60-9. <http://dx.doi.org/10.1016/j.jdent.2017.09.011> PMID: 28962842
- [45] Lopes LS, Calazans FS, Hidalgo R, *et al.* Six-month follow-up of cervical composite restorations placed with a new universal adhesive system: A randomized clinical trial. *Oper Dent* 2016; 41(5): 465-80. <http://dx.doi.org/10.2341/15-309-C> PMID: 27379834
- [46] Manarte-Monteiro P, Domingues J, Teixeira L, Gavinha S, Manso MC. Multi-Mode adhesives performance and success/retention rates in NCCs restorations: Randomised clinical trial one-year report. *Biomater Investig Dent* 2019; 6(1): 43-53. <http://dx.doi.org/10.1080/26415275.2019.1684199> PMID: 31998871
- [47] Manarte-Monteiro P, Domingues J, Teixeira L, Gavinha S, Manso MC. Universal adhesives and adhesion modes in non-cariou cervical restorations: 2-year randomised clinical trial. *Polymers* 2021; 14(1): 33. <http://dx.doi.org/10.3390/polym14010033> PMID: 35012056
- [48] Matos TP, Gutiérrez MF, Hanzen TA, *et al.* 18-month clinical evaluation of a copper-containing universal adhesive in non-cariou cervical lesions: A double-blind, randomized controlled trial. *J Dent* 2019; 90: 103219. <http://dx.doi.org/10.1016/j.jdent.2019.103219> PMID: 31629030
- [49] de Paris Matos T, Perdigão J, de Paula E, *et al.* Five-year clinical evaluation of a universal adhesive: A randomized double-blind trial. *Dent Mater* 2020; 36(11): 1474-85. <http://dx.doi.org/10.1016/j.dental.2020.08.007> PMID: 32933775
- [50] Oz FD, Dursun MN, Ergin E. Clinical performance of a "no wait" universal adhesive in noncariou cervical lesions: A two-year randomized controlled clinical trial. *J Adhes Dent* 2022; 24(1): 313-23. <http://dx.doi.org/10.3290/j.jad.b3240675> PMID: 35980240
- [51] Perdigão J, Kose C, Mena-Serrano AP, *et al.* A new universal simplified adhesive: 18-month clinical evaluation. *Oper Dent* 2014; 39(2): 113-27. <http://dx.doi.org/10.2341/13-045-C> PMID: 23802645
- [52] Merle CL, Fortenbacher M, Schneider H, *et al.* Clinical and OCT assessment of application modes of a universal adhesive in a 12-month RCT. *J Dent* 2022; 119: 104068. <http://dx.doi.org/10.1016/j.jdent.2022.104068> PMID: 35192908
- [53] Ruschel VC, Stolf SC, Shibata S, *et al.* Three-year clinical evaluation of universal adhesives in non-cariou cervical lesions. *Am J Dent* 2019; 32(5): 223-8. PMID: 31675189
- [54] Swift EJ Jr, Perdigão J, Heymann HO, *et al.* Eighteen-month clinical evaluation of a filled and unfilled dentin adhesive. *J Dent* 2001; 29(1): 1-6. [http://dx.doi.org/10.1016/S0300-5712\(00\)00050-6](http://dx.doi.org/10.1016/S0300-5712(00)00050-6) PMID: 11137632
- [55] İslatice Özkubat G, Yaman BC, Tepe H, Irmak Ö. Evaluation of restorations using universal adhesives in caries-free cervical region hard tissue losses according to FDI criteria. *Cumhuriyet Dent J* 2018; 21(4): 357-70. <http://dx.doi.org/10.7126/cumudj.467923>
- [56] Mahn E, Rousson V, Heintze S. Meta-analysis of the influence of bonding parameters on the clinical outcome of tooth-colored cervical restorations. *J Adhes Dent* 2015; 17(5): 391-403. <http://dx.doi.org/10.3290/j.jad.a35008> PMID: 26525003
- [57] Cuevas- Suárez CH, Rosa WLO. Bonding performance of universal adhesives: Na update systematic review and Meta-analysis. *J*

- Adhes Dent 2019; 21: 7-26.
<http://dx.doi.org/10.3290/jjad.a41975> PMID: 30799468
- [58] Rosa WLO, Piva E, Silva AF. Bond strength of universal adhesives: A systematic review and meta-analysis. J Dent 2015; 43(7): 765-76.
<http://dx.doi.org/10.1016/j.jdent.2015.04.003> PMID: 25882585
- [59] Arbildo H, Lamas-Lara C, Cruzado-Oliva F, Rosas-Prado C, Gómez-Fuerte A, Vásquez-Rodrigo H. Comparison of the clinical effect of the adhesive strategies of universal adhesives in the treatment of non-cariou cervical lesions. Systematic review and meta-analysis. J Oral Res 2018; 7(5): 210-22.
<http://dx.doi.org/10.17126/joralres.2017.049>
- [60] Dreweck FDS, Burey A, de Oliveira Dreweck M, Loguercio AD, Reis A. Adhesive strategies in cervical lesions: Systematic review and a network meta-analysis of randomized controlled trials. Clin Oral Investig 2021; 25(5): 2495-510.
<http://dx.doi.org/10.1007/s00784-021-03844-5> PMID: 33661448